

Production of Al-4.5% Cu Alloy Reinforced Fly Ash and SiC Hybrid Composite by Direct Squeeze Casting

G.N.Lokesh, M.Ramachandra, K.V.Mahendra

Abstract— Today the use of composites will be a clear choice in many instances especially in automobile and aerospace sector. Material selection in others will depend on factors such as working life span necessities, number of items to be produced, convolution of product shape, possible savings in assembly costs and on the experience & skills of the designer in drumming the optimum potential of composites. Composites produced using waste as reinforcements helps not only clearing environmental issues but also helps in increasing mechanical properties of the composites. One of the inexpensively available and also coming as waste form thermal power plant is fly ash. In the present investigation fly ash and SiC reinforced Al-4.5% Cu composites containing 2% fly ash with 2,4,6% SiC and 4% fly ash with 2,4,6% SiC fabricated by direct squeeze casting technique. The composites was analysed by measuring the hardness, tensile, compression, impact and wear behaviour. Microstructure of the composites was observed by scanning electron microscope (SEM). The results indicate that the hardness, tensile, compression, impact and wear resistance increases with increase in percentage of fly ash and SiC. Microstructure shows better bonding between matrix particle interface and no fracture observed.

Index Terms— Squeeze Casting, Fly Ash, Tensile Strength, Compression Strength, Wear.

I. INTRODUCTION

Aluminium-based alloys are widely used in automotive aerospace and industries because of their low densities and good mechanical and tribological properties [1]. However, the relatively poor convulsion resistance of aluminium alloys has restricted their uses in such engineering applications [2]. Conventional monolithic materials exhibit lower strength and stiffness and hence composites substitute and dominant for the past four decades [3]. Liquid metallurgy processes have some difficulties including the uniform dispersion of the ceramic particulates, extensive interfacial reactions, and particulate fracture during mechanical stirring, whereas powder metallurgy processes make easy, the uniform dispersion of the reinforcements and the control of interfacial reaction [4]. However, the liquid-phase processes have lower manufacturing cost and are nearer net shape than solid-phase processes [5].

Particulates or discontinuous-fiber reinforced Metal Matrix Composites (MMCs) present an opportunity for automotive manufacturers to improve performance and to reduce costs [6]. In liquid metallurgy, squeeze cast process is simple, economical and it can be automated easily [5]. The pressure infiltration process exhibit highest mechanical properties in cast products [7], whereas effect of squeeze pressure refines fine microstructure, low Coefficient of Thermal Expansion (CTE) [8], higher hardness, tensile strength [9], superior wear resistance [10], higher flexural strength and fatigue resistance [11], with higher fracture toughness and bending strength [12]. Fly ash particles are discontinuous dispersoids in the form of hollow spherical in shape used in MMCs, since they are low density and low-cost reinforcement available in large quantities as a waste in thermal power plants [13]. Fabrication of MMCs by casting processes is very promising for manufacturing near net shape components at a relatively low cost [14]. Al-fly ash MMCs are widely used in automobile applications due to its higher tensile, hardness, compression and wear resistance [15]. Al-alloy reinforced fly ash reveal superior damping characteristics [16] and increases mechanical properties [17]. Addition of fly ash decreases erosive wear but increases corrosion [18]. Squeeze cast of Al-fly ash is limited by many authors and J.Bienia et al. [14] compared gravity cast with squeeze casting of Al-fly ash reinforcement and stated that advantageous of squeeze cast for obtaining higher structural homogeneity with minimum porosity level, uniform distribution of fly ash and good interfacial bonding between matrix and fly ash. Al-alloy reinforced SiC particulates by squeeze casting is a promising composite accelerates hardness [19], tensile and fracture toughness [12], fatigue strength [20], flexural, stiffness and wear resistance [21] with low CTE and higher thermal conductivity [22]. The majority work reported in literature has been devoted to aluminium alloy with single reinforcement and not much work has been reported on the use of Al-alloy with two reinforcements casted by squeeze casting. Y. Q. Wang et al. [23] reinforced Al_2O_3 and SiC particulates in Al-alloy hybrid MMCs by squeeze cast and stated higher wear resistance and mechanical properties. In the present study an attempt has been made to squeeze cast Al-Cu alloy with two reinforcement fly ash and SiC to form hybrid MMCs with different weight percentage. The hardness, tensile, compression, impact and wear behaviour of hybrid MMCs were investigated. Microphotographs were taken by SEM to know the distribution of reinforcements.

Manuscript received December , 2013.

G.N.Lokesh, Mechanical Department, Acharya Institute of Technology, Bangalore-560107, India.

M.Ramachandra, Mechanical Department, BMS College of Engineering, Bangalore-560019, India.

K.V.Mahendra, Mechanical Department, Jyothy Institute of Technology, Bangalore-560062, India.

II. EXPERIMENTAL PROCEDURE

In this study, direct squeeze casting system was constructed for production of specimens. A stir casting setup which consisted of a resistance furnace and a stirrer assembly is used to synthesis the combination of matrix and reinforcements before squeeze. Al-4.5wt%Cu alloy commercially prepared was melted in a resistance heated muffle furnace and casted in a crucible. Table 1 shows the chemical composition of base alloy, analysed by optical emission spectrometer. The density of fly ash measured is 2.1 g/cm³ with the particle size varying between 49 and 60µm. SiC particle size which is used to fabricate the composite had an average of 60µm and density is 3.2g/cm³. Fig.1 shows the SEM micrographs of fly ash particulates.

Table 1. The chemical composition of the base alloy (wt. %)

Cu	4.51
Mg	0.061
Si	0.52
Fe	0.59
Mn	0.13
Ni	0.06
Pb	0.03
Sn	0.02
Ti	0.012
Zn	0.12
Al	Balance

Initially, Al-4.5wt%Cu alloy which is widespread commercial applications was charged into the crucible and heated to about 750°C till the entire alloy in the crucible was melted. The fly ash particles were preheated to 210°C for two hours to remove moisture. The SiC particles were heated at 400°C temperature for 2 h before addition into the melt. The cast iron mold of size 50mm diameter with 200mm length was used for the preparation of cast blanks. After the molten metal was fully melted, solid dry hexachloroethane degassing tablet was added to reduce the porosity. The stirrer was lowered into the melt slowly to stir the molten metal at the speed of 450 rpm. Various stirrer speeds, tilt angles and movement of stirrer from top to bottom in the crucible were used to obtain vortex strong enough to disperse the reinforcements into the melt [16]. The preheated fly ash and SiC particles were added to the vortex between liquidus and solidus temperatures at the rate of 25g/min during the stirring time with Mg (0.6wt %) were also added to ensure good wettability of particles[24]. The stirring was continued for another 1minute even after the completion of particle feeding. The temperature was also monitored simultaneously during stirring. Split cast iron die and tool steel ram were preheated to 400°C to avoid premature chilling. After through mixing of matrix and reinforcements, the melt was poured into preheated die cavity and solidification was carried out with a squeeze pressure of 110MPa for a period between 120 and 180 seconds [12]. The chemical composition of samples casted is shown in Table 2. As the matrix alloy is age hardening, the composites produced were subjected to T6 heat treatment [6, 25]. The castings were heated to 450°C for 12 hours, quenched in 100°C water and reheated to 170°C for 16hours and cooled in the furnace

temperature. Hardness measurements were performed using a Brinell hardness tester with a load of 10kgf as per ASTM-E10-01. Hardness values were averaged over eight measurements taken at different points on the cross-section. Tensile tests were carried out using samples prepared according to ASTM-E-8M-09 standard. These tests were conducted using a computerized universal testing machine (UTM) with 60KN capacity. Similarly compression strength were determined using a computerized UTM with an electronic extensometer as per ASTM-E9-89A standards. Online plotting of load versus extension was done continuously through a data acquisition system. Impact specimen was cut as per ASTM-E23 by diamond blade using CNC machine. Wear test was carried out using a computerized pin on a disc wear testing machine under ambient temperature conditions. Wear pins of 8mm diameter and 30mm heights were prepared and subsequently the weight loss of the materials was determined. Micro photographs were taken after wear test of each sample for SEM to examine the effect of the percentage of particle distribution.

Table 2. Measured chemical composition of squeeze cast samples (wt.%)

Sample		Composition
Sample 1	Base alloy	Al-4.5wt%.Cu alloy
Sample 2	Composite 1	2wt%Fly ash, 2wt%.SiC,
Sample 3	Composite 2	2wt%Fly ash, 4wt%.SiC
Sample 4	Composite 3	2wt%Fly ash, 6wt%.SiC,
Sample 5	Composite 4	4wt%Fly ash, 2wt%.SiC,
Sample 6	Composite 5	4wt%Fly ash, 4wt%.SiC,
Sample 7	Composite 6	4wt%Fly ash, 6wt%.SiC,

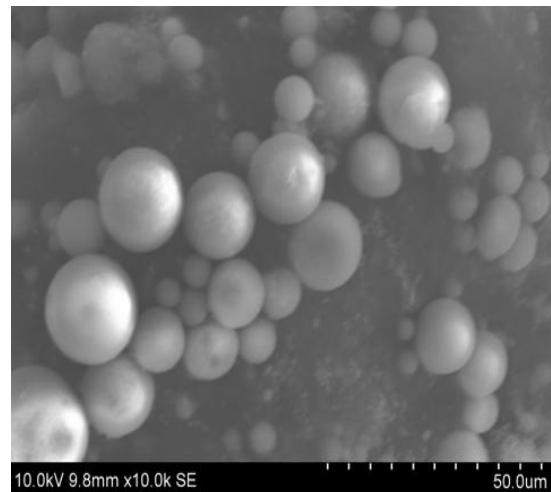


Fig.1 SEM of fly ash particulates

III. RESULTS AND DISCUSSION

A. Hardness

From Fig.2, the hardness of squeeze cast composite is higher than that of matrix alloy by about 5.5% approximately. The hardness increases with increase percentage of reinforcements which is in par with literature [24]. The application of pressure during solidification in squeeze casting minimizes porosity and makes the metal

denser, making the matrix to resist surfacial plastic deformation, rendering higher hardness to the matrix. The dispersion of fly ash and SiC particles enhances the hardness, as particles are harder than Al alloy. The materials render their inherent property of hardness to the soft matrix. The hardness in squeeze casting conditions may be due to combined effect of denser matrix and hard ceramic particles [27]. The peak hardness of 114BHN was found to be for an addition of 4wt.% fly ash and 6wt% SiC particles in squeeze cast condition.

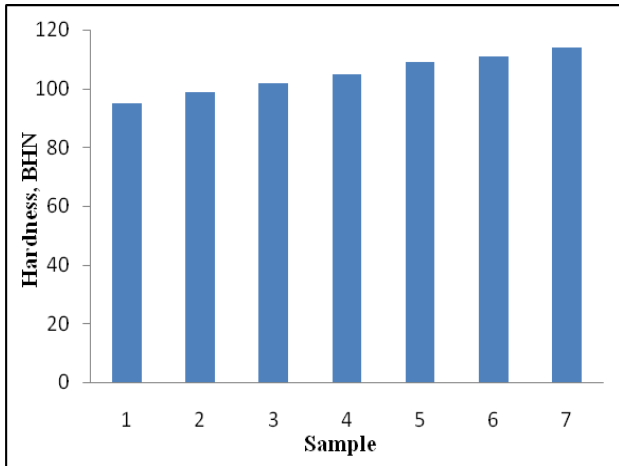


Fig. 2 Hardness of squeeze cast of base alloy and composite

B. Tensile strength

The influence of fly ash and hard SiC particulate content on the Ultimate tensile strength (UTS) of the MMC is shown in Fig.3. It is noted that the UTS increases with the addition of reinforcements. The UTS shows the peak value of 160MPa for 4wt.% fly ash and 6wt.% SiC and shows an increase of strength to 45.5% when compared to squeeze cast of base alloy. This is due to the hard and lighter microsphere of fly ash, which act as barriers to the movement of dislocation and refines the structure of matrix [28].

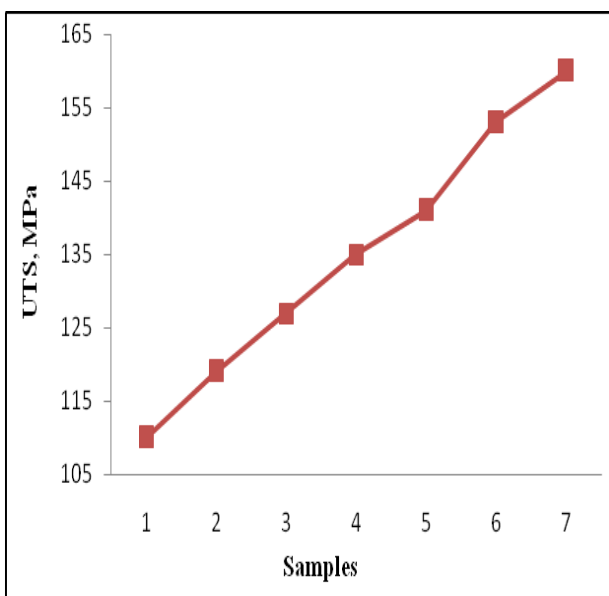


Fig. 3 Ultimate tensile strength of squeeze cast base alloy and composite

C. Compression strength

Fig.4 shows the results obtained from uniaxial compression as a function of fly ash and SiC particulate. Increase in percentage of fly ash and SiC increases the compression strength of composites. This is due to the hardening of the base alloy by fly ash particulates.

The SiC reinforcement has highest weight percentage and this may increase the density of the material which cause in increase in compressive strength. The squeeze cast exhibit higher compression strength and this may be due to compaction pressure applied during squeeze made the casting finer grain size and low porosity. The compression strength of squeeze cast base alloy is 564MPa and that of 4wt.% fly ash and 6wt.% SiC is 778MPa, which is 38% increase in strength. This could be due to the applied pressure while squeezing. The applied pressure attributed to eliminating of micro-pores in the alloy and microstructure refining enhancement of solubility of solute [29].

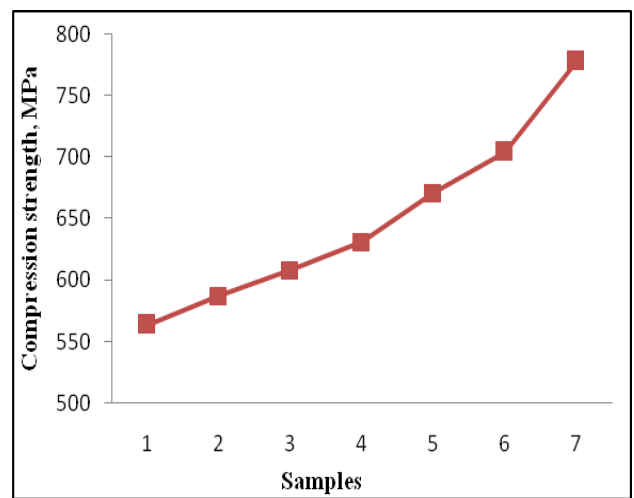


Fig. 4 Compression strength of squeeze cast base alloy and composite

D. Impact strength

From Fig. 5 the impact strength also increases with increasing fly ash and SiC content.

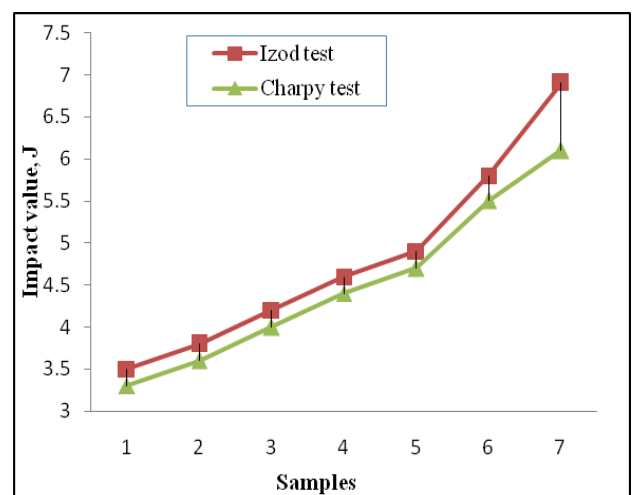


Fig. 5 Impact strength of squeeze cast base alloy and composite

This may be due to the presence of hard fly ash and SiC particulates. The impact strength shows higher values for higher percentage of reinforcements. This is due to the applied pressure during squeeze which gives homogeneous crystal structure and dendrite arms were broken down and fine-grained equiaxed microstructure will be obtained by squeeze casting.

E. Wear behaviour

Fig. 6 shows the weight loss during wear test for different weight percentage of Al-4.5wt.%Cu alloy and Al-4.5wt.%Cu alloy reinforced fly ash and SiC MMCs for 10N load. Dry sliding wear behaviour of matrix alloy reinforced fly ash and SiC shows reasonable increase in wear resistance.

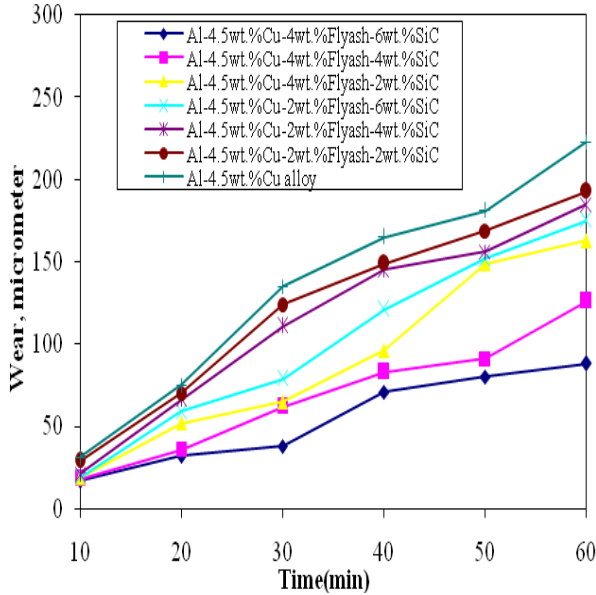


Fig. 6 Wear vs. time at various percentages of fly ash and SiC at 10 N load of casting

It is observed that addition of 4wt. % fly ash and 6wt. %.SiC shows lesser wear than other composites. The highest weight loss is distinct for matrix alloy and linearly the weight loss decreased by increasing the percentage of reinforcements. The wear resistance of the composites is considerably improved due to the addition of 6wt.% SiC particle. Also presence of 4wt.% fly ash strengthen the matrix and hence more wear resistance is observed and therefore volume of wear debris decrease with increasing percentage of reinforcements.

F. Microstructure

It can be seen in Figures (7 and 8) that, the presence of grooves of varying sizes was observed frequently on the worn surface. The worn debris particles are likely to act as third body abrasive particles. The fly ash and SiC particles trapped between the specimen and counterface cause microploughing on the contact surface of the composite [30]. The wearing surface is characterized by a significant transfer of material between the sliding surfaces. Fly ash and SiC could be dispersed inside the matrix alloy with better bonding due to which the wear resistance occurred. Also it is observed that matrix alloy reinforced up to 4wt. % fly ash and 6wt. % SiC for a load of 10N, there is no fracture initiation at matrix particle interface.

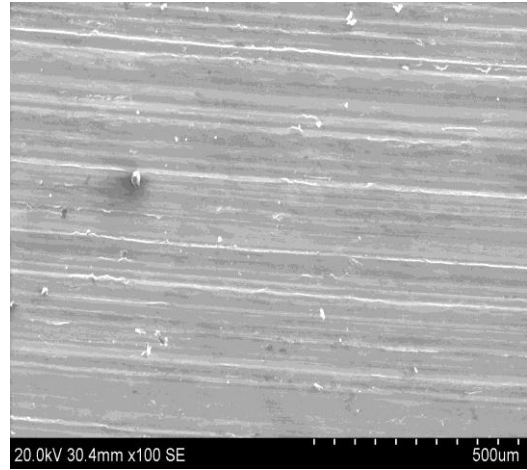


Fig. 7 SEM micrograph of worn sample of matrix reinforced 2%flyash, 6%SiC at 10N

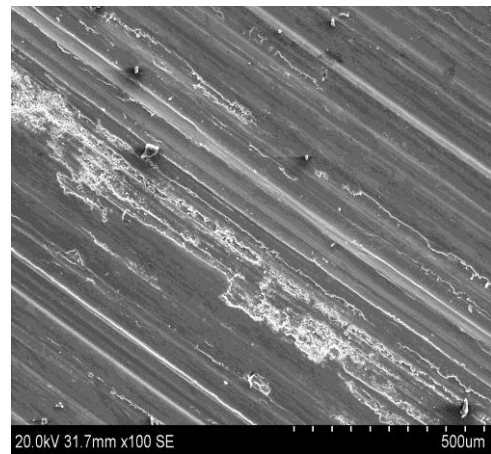


Fig. 8 SEM micrograph of worn sample of matrix reinforced 4%flyash, 6%SiC at 10N

IV. CONCLUSION

Effect of squeeze cast and addition of reinforcements on mechanical properties of fly ash and SiC particulates reinforced Al-4.5wt.%Cu composite have been investigated in this paper. The test results showed that the fly ash up to 4% and SiC up to 6% by weight can be successfully added to Al-4.5wt.%Cu alloy by squeeze casting route to produce composites. Addition of flyash and SiC improves the hardness of the composite. Ultimate tensile strength, compression and impact strength also increases with an increase of fly ash and SiC particulates. The wear resistance increases with an increased percentage of flyash and SiC particulates. Microphotographs shows better bonding between matrix, fly ash and SiC with no fracture observed at matrix particle interface. Overall, Al-4.5wt.%Cu alloy can be considered as a suitable matrix for the development of fly ash and SiC reinforced aluminium based composites by squeeze casting.

V. ACKNOWLEDGEMENT

The authors would like to extend their acknowledgement to the Visvesvaraya Technological University, Belgaum, India for providing the facilities and support to accomplish this research. The authors further extend their sincere thanks to Jyothy Institute of Technology, and BMS College of Engineering, India, for providing lab facilities. In addition,

G.N.Lokesh is grateful to NIT, Calicut, for providing laboratory facility for getting SEM photographs.

REFERENCES

- [1] I.A. Ibrahim, F.A. Mohamed and E.J. Lavernia, Particulate reinforced metal matrix composites a review, *Journal of Materials Science* 26 (1991), pp.1137-1156.
- [2] S.C. Tjong, K.C. Lau, Properties and abrasive wear of TiB₂/Al-4%Cu composites produced by hot isostatic pressing, *Composites Science and Technology* 59 (1999), pp. 2005–2013.
- [3] Young-Ho Seo, Chung-Gil Kang, The effect of applied pressure on particle-dispersion characteristics and mechanical properties in melt-stirring squeeze-cast SiCp/Al composites, *Journal of Materials Processing Technology* 55 (1995), pp. 370-379.
- [4] I. C. Stone and P. Tsakiropoulos, The effect of the spatial distribution of reinforcement on the fabrication and heat treatment of (Al-4wt.%Cu)-SiC particle metal matrix composites, *Materials & Engineering, A* 189 (1994), pp. 285-290.
- [5] T.R. Vijayaram, S. Sulaiman, A.M.S. Hamouda, M.H.M. Ahmad, Fabrication of fiber reinforced metal matrix composites by squeeze casting technology, *Journal of Materials Processing Technology* 178 (2006), pp. 34–38.
- [6] T.P.D. Rajan, R.M. Pillai, B.C. Pai, K.G. Satyanarayana, P.K. Rohatgi, Fabrication and characterisation of Al-7Si-0.35Mg/fly ash metal matrix composites processed by different stir casting routes, *Composites Science and Technology* 67 (2007), pp. 3369–3377.
- [7] M.R. Ghomashchi, A. Vikhrov, Squeeze casting: an overview, *Journal of Materials Processing Technology* 101 (2000), pp.1-9.
- [8] P. K. Rohatgi, N. Gupta, Simon Alaraj, Thermal Expansion of Aluminum-Fly Ash Cenosphere Composites Synthesized by Pressure Infiltration Technique, *Journal of composite materials*, Vol. 40, No. 13 (2006), pp.1163-1174.
- [9] Young-Ho Seo, Chung-Gil Kang, The effect of applied pressure on particle-dispersion characteristics and mechanical properties in melt-stirring squeeze-cast SiCp/Al composites, *Journal of Materials Processing Technology*, 55 (1995), pp. 370-379.
- [10] Adem Onat, Mechanical and dry sliding wear properties of silicon carbide particulate reinforced aluminium-copper alloy matrix composites produced by direct squeeze casting method, *Journal of Alloys and Compounds*, 489 (2010), pp. 119–124.
- [11] Cevdet Kaynak, Suha Boylu, Effects of SiC particulates on the fatigue behaviour of an Al-alloy matrix composite, *Materials and Design*, 27 (2006), pp. 776–782.
- [12] Olivier Beffort, Siyuan Long, Cyril Cayron, Jakob Kuebler, Philippe-Andre Buffat, Alloying effects on microstructure and mechanical properties of high volume fraction SiC-particle reinforced Al-MMCs made by squeeze casting infiltration, *Composites Science and Technology* 67 (2007), pp. 737–745.
- [13] Garios Itskos, P.K.Rohatgi, A. Moutsatsou, C.Vasilatos, John.D. Defow, Nikolas Koukouzas, Pressure Infiltration Technique for the Synthesis of A356 Al/fly Ash Composites: Microstructure and Tribological Performance, *World of Coal Ash (WOCA) Conference - May 9-12, 2011, in Denver, CO, USA.*
- [14] J. Bienia, M. Walczak, B. Surowska, J. Sobczaka, Microstructure And Corrosion Behaviour Of Aluminium Fly Ash Composites, *Journal of Optoelectronics and Advanced Materials*, Vol. 5, No. 2, June 2003, pp. 493-502.
- [15] P. Shanmugasundaram, R. Subramanian and G. Prabhu, Some Studies on Aluminium – Fly Ash Composites Fabricated by Two Step Stir Casting Method, *European Journal of Scientific Research*, ISSN 1450-216X Vol.63 No.2 (2011), pp.204-218.
- [16] Sudarshan, M.K. Surappa, Synthesis of fly ash particle reinforced A356 Al composites and their characterization, *Materials Science and Engineering, A* 480 (2008), pp. 117–124.
- [17] K.V. Mahendra, K. Radhakrishna, Fabrication of Al-4.5% Cu alloy with fly ash metal matrix composites and its characterization, *Materials Science-Poland*, Vol. 25, No. 1(2007), pp.57-68.
- [18] M. Ramachandra, K. Radhakrishna, Effect of reinforcement of fly ash on sliding wear, slurry erosive wear and corrosive behavior of aluminium matrix composite, *Wear* 262 (2007), pp. 1450–1462.
- [19] Adem Onat, Hatem Akbulut, Fevzi Yilmaz, Production and characterization of silicon carbide particulate reinforced aluminium-copper alloy matrix composites by direct squeeze casting method, *Journal of Alloys and Compounds*, 436 (2007), pp. 375–382.
- [20] N.E. Bekheeta, R.M. Gadelrabb, M.F. Salah, A.N. Abd El-Azim, The effects of aging on the hardness and fatigue behavior of 2024 Al alloy/SiC composites, *Materials and Design*, 23 (2002), pp. 153-159.
- [21] S. Long, O. Beffort, C. Cayron and C. Bonjour, Microstructure and mechanical properties of a high volume fraction SiC particle reinforced AlCu4MgAg squeeze casting, *Materials Science and Engineering*, A269 (1999), pp.175–185.
- [22] Jung-Moo Lee, Sang-Kwan Lee, Sung-Jin Hong, Yong-Nam Kwon, Microstructures and thermal properties of A356/SiCp composites fabricated by liquid pressing method, *Materials & Design*, Volume 37, May 2012, pp. 313-316.
- [23] Y.Q. Wang, A.M. Afsar, J.H. Jang, K.S. Han, J.I. Songa, Room temperature dry and lubricant wear behaviors of Al₂O₃/SiCp/Al hybrid metal matrix composites, *Wear* 268 (2010), pp. 863–870.
- [24] Cevdet Kaynak, Suha Boylu, Effects of SiC particulates on the fatigue behaviour of an Al-alloy matrix composite, *Materials and Design* 27 (2006), pp.776–782.
- [25] Jae-Ho Jang, Dae-Geun Nam, Yong-Ho Park, Ik-Min Park, Effect of solution treatment and artificial aging on microstructure and mechanical properties of Al-Cu alloy, *Transactions of Nonferrous Metals Society of China*, Volume 23, Issue 3, March 2013, Pages 631-635.
- [26] K.V.Mahendra, K.Radhakrishna, Characterization of Stir Cast Al-Cu-(fly ash + SiC) Hybrid Metal Matrix Composites, *Journal of Composite Materials*, Vol 44, April(2010), pp.989-1005.
- [27] A.K. Banerjee, P.K. Rohatgi, W. Reif, in: *Proceedings of the Eighth Symposium in Advanced Material Research and Development for Transport-Composites*, 1985, Strausbourg, France, November 1985.
- [28] Suresh N, Venkateswaran S, Seetharamu S, Influence of Cenospheres of fly ash on the mechanical properties and wear of permanent moulded eutectic Al-Si alloys, *Materials Science-Poland*, Vol.28, No.1,(2010), pp.55-65.
- [29] LI Run-Xia, LI Rong-de, Bai Yan-hua, QU Ying-dong, Yuan Xiao-guang, *Transaction of nonferrous metals society of china*,20 (2010), pp.59-63.
- [30] G.N.Lokesh, M.Ramachandra, K.V.Mahendra, T.Sreenith, Effect of Hardness, Tensile and Wear Behavior of Al-4.5wt%Cu Alloy/Fly ash/SiC Metal Matrix Composites, *International Journal of Modern Engineering Research*, Vol.3, Issue.1, Jan-Feb. (2013), pp. 381-385.



G. N. Lokesh is Assistant Professor in the Dept. of Mechanical Engineering, Acharya Institute of Technology Bangalore-560107, India. He received his Bachelor of Engineering in Mechanical Engineering from Bangalore University in 1998. He received his M.Tech. from Kuvempu University in 2001. He is currently pursuing his Ph.D. in Mechanical Engineering at Visvesvaraya Technological University, Belgaum, India, started since 2010 under the supervision and guidance of Dr. M. Ramachandra and Dr. K.V. Mahendra. His research interests include characterization of Hybrid Metal Matrix Composites and its Secondary process. He has also presented more than fifteen research articles in national and international conferences and published many journals.



Dr. M. Ramachandra working as Professor in the Dept. of Mechanical Engineering, B.M.S. College of Engineering, Bangalore-560019, India. He received his BE in Mechanical Engineering from Mysore University in 1987, M.Tech. from University B. D. T. College of Engineering, Kuvempu University in 1992 and Ph.D. in Mechanical Engineering from VTU, Belgaum in 2007. He is guiding five Ph.D. Research scholars and presented more than fifteen research articles in national, international conferences and many journals. His research interests include characterization of Metal Matrix Composites and Nano-composites using fly ash as reinforcements.



Dr. K. V. Mahendra working as a principal in Jyothy Institute of Technology, Kanakapura Road, Bangalore-560062, India. He received his BE in Mechanical Engineering from Gulbarga university, Master of Engineering in Metal Casting Science and Engineering from Bangalore University and Ph.D. in Mechanical Engineering from VTU, Belgaum in 2007. He is an active member of several professional bodies like ISTE, IIF FM & FP, TSI and IE. He is guiding more than five Ph.D. Research scholars under Visvesvaraya Technological University, Belgaum, India. He has presented more than fifteen research articles in national and international conferences and published many journals. His research interests include development of rolled products of MMC for automobile industries and study of tribological behaviors of hybrid MMC.