

The Use of Recycled Steel Bars as Shear Reinforcement Swimmer Bars in Reinforced Concrete Beams

Moayyad M. Al-Nasra

Abstract— The discarded steel reinforcement bars can be either sent to steel plant to be melted and reproduced, or reused as steel reinforcement again. The main sources of the recycled steel bars are the demolished structures, damaged bars or collapsed structures. There is little evidence to trust the use of the recycled steel bars as a replacement of new steel bars. Engineers often question the safety of the structures built with recycled steel bars. In order to address the concern of the engineers, the recycled bars must be evaluated and categorized and eventually given an equivalent new bar label. Additional factor of safety could be used for uncertainty. In this study the recycled steel bars are used as spliced swimmer bars for shear reinforcement in reinforced concrete beams. The used bars in this study are classified as class-A recycled bars. There are several alternatives to the traditional stirrups in reinforced concrete beams. This study focuses on providing other options other than the stirrups. Due to the unsafe mode of shear failure in reinforced concrete beams, designers may find themselves reluctant to use higher factor of safety. Shear failure in reinforced concrete beams is one of the most undesirable modes of failure due to its rapid progression. This sudden type of failure made it necessary to explore more effective ways to design these beams for shear. The cost and safety of shear reinforcement in reinforced concrete beams led to the study of other alternatives. In this study two different types of shear reinforcements are used to study the effect of each type of shear reinforcement on the shear performance of reinforced concrete beams. The first type is reinforced by traditional stirrups, while the other type is reinforced by spliced swimmer bars. Two beams were prepared with spliced swimmer bars; the first is made from recycled steel bars, and the other is made from brand new bars. The beam made from recycled spliced swimmers is compared with the other two beams. Beam shear strength as well as beam deflection are the main two parameters considered in this study. The swimmer bar system is a new type of shear reinforcement. Splicing swimmer bars concept is a solution to the welding problem associated with old types of swimmer bars. Special shapes of swimmer bars are used for in this study such that the swimmer bars are spliced with the longitudinal flexural bars. Regardless of the number of swimmer bars used in each inclined plane, the swimmer bars form plane-crack interceptor system instead of bar-crack interceptor system when stirrups are used. The results of the three tested beams will be presented and discussed in this study. Also the deflection of the beams due to the gradual applied load is monitored and discussed. Cracks will be monitored and recorded during the beam test as the applied load increases.

Index Terms— Deflection, Shear, Stirrup, swimmer bars.

Manuscript published on 30 December 2015.

* Correspondence Author (s)

Dr. Moayyad Al-Nasra, Professor, Civil Engineering Department, Applied Science University, Amman, Jordan. This research project is sponsored by the Applied Science University, Amman, Jordan.

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an open access article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>.

I. INTRODUCTION

The discarded steel reinforcement can be used as recycled steel bars after preparing and rehabilitating process in order to make these bars fit to be used again. The sources of these recycled bars vary, depending on the current situation. The recycled bars used in this study came from demolished buildings. The recycled bars are classified based on the bars condition, and the degree of damage. Table 1 shows a brief description of the classification process. At the end of the classification process of the recycled bar, an equivalent new bar size is given to that bar with some additional recommendations, specifications as well as limitations for future use of that bar. There is always another option available, which is sending these used bars to a steel factory to be used as scrap metal. Usually, the scrap metals are recycled by the process of re-melting and reforming under

No.	Bar Classification Code	General Description
1	A	No visual corrosion, no measurable change in bar diameter, and the no damage to the deformed ribs
2	B	No visual corrosion, and no measurable change in bar diameter, but there is visual damage on the bar ribs
3	C	Minor corrosion, with diameter reduction less than 5%. Obvious damage to the bar ribs.
4	D	Substantial corrosion, with diameter reduction less than 25% of the original diameter, and no visible ribs
5	E	Excessive corrosion, with diameter reduction exceeds 25%

high temperature. This process is deemed to be relatively expensive option, and involves many steps that may not be available to the average construction worker.

Table 1: Classification summary of recycled steel bars, the cold process

Class A bars, after rehabilitation process, can be used in shear or flexure, and the equivalent bar size would be, most likely, the same size of the recycled bar. The equivalent bar size given here in this process is given upon thorough inspection and recommendation of a certified engineer.



The damage in the bar ribs calls for increase in the development length due to the reduced bonding potential of the recycled bars. In this particular case, there will be recommendation for an equivalent bar size, as well as recommendations on the future use of these recycled bars. The used bars subjected to substantial corrosion damage can be given an equivalent bar size less than the original bar size. These bars should be used in any structural member of critical sections.

The recycled bars used in this study are classified as Class A bars. The bars exhibit no visible corrosion and no damage to the bar ribs. Figure 1 shows samples of the recycled bars used, and prepared. These bars were also tested in tension to make sure that there is no decrease in the bar strength. The test includes also sample of steel bars of the same size as the recycled bars. These brand new bars are used as controlling samples. The test results of the recycled bars are compared with the test results of the brand new bars. The test results showed that there is no measurable decrease in strength of the recycled bars.



Figure 1: Samples of recycled bars

There are several objectives that a designer must consider when designing reinforced concrete beams including safety, durability and cost. Sudden failure due to shear low strength is not desirable mode of failure. The reinforced concrete beams are designed primarily for flexural strength and shear strength. Beams are structural members used to carry loads primarily by internal moments and shears. In the design of a reinforced concrete member, flexure is usually considered first, leading to the size of the section and the arrangement of reinforcement to provide the necessary resistance for moments. For safety reasons, limits are placed on the amounts of flexural reinforcement to ensure ductile type of failure. Beams are then designed for shear. Since shear failure is frequently sudden with little or no advanced warning, the design for shear must ensure that the shear strength for every member in the structure exceeds the flexural strength. The shear failure mechanism varies depending upon the cross-sectional dimensions, the geometry, the types of loading, and the properties of the member.

Reinforced concrete beams must have an adequate safety margin against bending and shear forces, so that it will perform effectively during its service life. At the ultimate limit state, the combined effects of bending and shear may exceed the resistance capacity of the beam causing tensile

cracks. The shear failure is difficult to predict accurately despite extensive experimental research. Retrofitting of reinforced concrete beams with multiple shear cracks is not considered an option (Al-Nasra and Wang, 1994)

Beams subjected to considerable shear forces exhibit diagonal cracks near the beam support, where the shear forces are usually critical. Excessive applied shear forces allows the crack to propagate at a faster rate compared with the bending cracks. Also the width of the diagonal cracks is usually higher than the bending cracks. Shear reinforcements are provided to carry some of the shear forces and prevent the formation of the diagonal cracks. Usually in the civil engineering practice, steel stirrups are used for this purpose. The steel stirrups are placed vertically and upright. The spacing of these stirrups is used as the parameter of design for the applied shear forces.

Bent up bars may also be used to carry some of the shear forces. Commonly, these bent up bars are the positive longitudinal steel reinforcement bent near the support to join the negative steel. Due to construction cost and other technical considerations engineers preferred not to use bent up bars

In this study, three reinforced concrete beams were tested using the new shear reinforcement swimmer bar system made of recycled bars and brand new bars and, the traditional stirrups system. Several shapes of swimmer bars were used before to study the effect of swimmer bar configuration on the shear load carrying capacity of the beams (Al-Nasra et al 2013). Only the splicing swimmer bars will be presented in this study. The first beam, BC, is used as a reference control beam where stirrups are used as shear reinforcement. The stirrups are made of brand new bars. The other beam was reinforced by splicing swimmer bars made from recycled bars. The beam designated as SSB beam is reinforced by swimmer bars spliced with the longitudinal steel reinforcement. Extra stirrups were used to make sure that the prepared beam will fail by shear in the swimmer bars side. In this investigation, all of the beams are supposed to fail solely in shear, so adequate amount of tension reinforcement were provided to give sufficient bending moment strength. This study aims at investigating a new approach of design of shear reinforcement through the use of splicing swimmer recycled bars provided in the high shear region. The main advantages of this type of shear reinforcement system are: flexibility, simplicity, efficiency, speed of construction, and cost.

Al-Nasra and Asha (2013) studied the use of swimmer bars welded to the longitudinal steel reinforcement, and concluded that the beam reinforced with welded swimmers bars exhibit better shear resistance compared with the control sample beam reinforced with regular stirrups. Also Al-Nasra and Asha (2015) studied the use of the spliced swimmer bars. They concluded that the splicing swimmer bars performs relatively well compared with the welded swimmer bars.

Piyamahant (2002) showed that the existing reinforced concrete structures should have stirrup reinforcement equal to the minimum requirement specified the code. The theoretical analysis shows that the amount of stirrup of 0.2% is appropriate.

The paper concluded that small amount of web reinforcement is sufficient to improve the shear carrying capacity. The study focused on the applicability of the superposition method that used in predicting shear carrying capacity of reinforced concrete beam with a small amount of web reinforcement at the shear span ratio of 3. Also the failure mechanisms were considered when small amount of stirrup used.

Sneed, and Julio (2008) discussed the results of experimental research performed to test the hypothesis that the effective depth does not influence the shear strength of reinforced concrete flexural members that do not contain web reinforcement. The results of eight simply supported reinforced concrete beam tests without shear and skin reinforcement were investigated. The beams were designed such that the effective depth is the variable while the values of other traditionally-considered parameters proven to influence the shear strength (such as the compressive strength of concrete, longitudinal reinforcement ratio, shear span-to-depth ratio, and maximum aggregate size) were held constant. The values selected for the parameters held constant were chosen in an attempt to minimize the concrete shear strength.

Noor (2005) presented several results of experimental investigation on six reinforced concrete beams in which their structural behavior in shear was studied. The research conducted was about the use of additional horizontal and independent bent-up bars to increase the beam resistance against shear forces. The main objectives of that study were studying the effectiveness of adding horizontal bars on shear strength in rectangular beams, the effectiveness of shear reinforcement, and determining the optimum amount of both types of shear reinforcement to achieve a shear capacity similar to that of a normal links system. From experimental investigation of the system it was found that, the use of independent horizontal and bent-up bars as shear reinforcement were stronger than conventional shear reinforcement system.

II. SWIMMER BARS

A swimmer bar is a small inclined bar, with its both ends bent horizontally for a short distance, welded, bolted or spliced at the top and the bottom with the longitudinal steel reinforcing bars. There are three major standard shapes; single swimmers, rectangular shape, and rectangular shape with cross bracings. Several additions to these standard shapes can be explored, such as addition of horizontal stiffener bars in the rectangular shapes, dividing the large rectangle horizontally into smaller rectangles. Additional swimmer bars can also be used. By adding one more swimmer bar to the rectangular shape, the large rectangular shape will be divided vertically into two rectangles. The addition of two more swimmer bars at the same section will divide the large rectangle vertically into four small rectangles. A combination of horizontal bars and additional swimmer bars may also be explored. This swimmer bar system is integrated fully with the longitudinal steel bars. Several options of the swimmer bar systems are used in order to improve the shear performance of the reinforced concrete beams, reduce the amount of cracks, reduce the width and the length of cracks and reduce overall beam

deflection. Different bar diameters can be used in order to add stiffness to the steel cage, and increase shear strength of the reinforced concrete beam.

III. ACI CODE PROVISION FOR SHEAR DESIGN

According to the ACI Code (ACI 2011), the design of beams for shear is to be based on the following relation:

$$V_u \leq \phi V_n \quad (1)$$

Where: V_u is the total shear force applied at a given section of the beam due to factored loads and $V_n = V_c + V_s$ is the nominal shear strength, equal to the sum of the contribution of the concrete and the web steel if present. Thus for vertical stirrups

$$V_u \leq \phi V_n + (\phi A_v f_y t d) / S \quad (2)$$

and for inclined bars

$$V_u \leq \phi V_n + (\phi A_v f_y t d (\sin \alpha + \cos \alpha)) / S \quad (3)$$

Where: A_v is the area of one stirrup, α is the angle of the stirrup with the horizontal, S is the stirrup spacing, and $f_y t$ is the yield strength.

The nominal shear strength contribution of the concrete (including the contributions from aggregate interlock, dowel action of the main reinforcing bars, and that of the un-cracked concrete) can be simplified as shown in Eq. 4.

$$V_c = 0.17 \lambda \sqrt{f_c'} (b_w d) \quad (4)$$

Where: b_w and d are the section dimensions, and for normal weight concrete, $\lambda = 1.0$. This simplified formula is permitted by the ACI code expressed in metric units (Nawy, 2009).

If you are using *Word*, use either the Microsoft Equation Editor or the *MathType* add-on (<http://www.mathtype.com>) for equations in your paper (Insert | Object | Create New | Microsoft Equation or MathType Equation). "Float over text" should *not* be selected.

IV. TESTED BEAMS

This study focused on investigating the shear strength of two different types of reinforced concrete beams; beams reinforced with regular stirrups made from brand new bars, and beams reinforced with spliced swimmer recycled bars and spliced swimmer new bars. All specimens were of the same size and reinforced with identical amount of longitudinal steel. The amount of longitudinal steel used in this study is, by design, selected to make sure that the failure will be dictated only by shear and not by bending. The beams were tested to fail due to two point loads by shear given the ratio of a shear span to effective depth of 2.5. The compressive strength of concrete is measured according to ASTM C 192-57. Twelve concrete samples were prepared. The compressive strength of concrete is measured at the 28th day. The concrete compressive strength results range between 27.1 N/mm² to 29.0 N/mm². The variables in these specimens are the shear reinforcement systems.

All of the tested beams are of the same dimension 2000 mm length, 200 mm width and 250 mm depth. The effective length was also kept at constant value of 1800 mm, which is the distance between the supports. Summary of shear reinforcement system for each specimen is given in Table 2. All tested beams were designed with 3 ϕ 14 top steel and 4 ϕ 16 bottom steel reinforcement. The reference beam, BC, was designed with 10 ϕ 8 mm at 600 mm spacing vertical stirrup at either side.

Figure 2 shows a typical steel cage used in beams reinforced with recycled spliced swimmer bars. Figure 3 shows two swimmer bars spliced together. The weights of the steel cages were intentionally designed to be very close in numbers. The erection and assembling time of the spliced swimmer bars beam is relatively less than the erection and assembling time of the control beam reinforced by brand new stirrups.

Table 2: Summary of steel reinforcement used in the tested beams

Beam No.	Shear Reinforcement		Steel Cage Weight (N)
	Vertical stirrup	Bent-up Bars	
BC	10 ϕ 8 mm spaced @ 60 mm at shear sides	-	255
R-SSB	-	Three recycled spliced swimmers, ϕ 10 mm spaced @ 275 mm	247
N-SSB	-	Three new spliced swimmers, ϕ 10 mm spaced @ 275 mm	251



Figure 2: Typical steel cage reinforcement of the beam reinforced with spliced swimmer bars.



Figure 3: Recycled spliced swimmer bars of new designed shape

V. TEST PROCEDURE

Prior to testing, the surface of the specimens was painted with white emulsion for the purpose of making the cracks more visible and easy to track. At the age 28 days, the reinforced concrete beams were prepared for testing. Marking lines were used to show the location of the point loads, supports and the mid-span of the beam in order to make it easier to install the beams on the testing machine. The test was carried out with the specimen placed horizontally in a simple loading arrangement. The beams were supported by solid round steel on their two edges that can be considered as simply supported beam members. All the beams were designed to ensure the beams will only fail in shear rather than in flexure.

To ensure that shear cracks will occur near the support, two point loads were applied symmetrically to the beam with a_v less than 2.5d. In this testing, $a_v \approx 550$ mm, where a_v is shear span (the distance from the point of the applied load to the support), and d is the effective depth of a beam.

A loading jack was placed at the mid-span position above the beam. The load was applied by jacking the beam against the rig base member at a constant rate until the ultimate load capacity of the beam was reached. A universal column section was used to transfer the load to the beam at two point loads via transfer girder. A reasonable time interval was allowed in between each 20.0 kN load increments for measuring deflections, marking cracks, measuring the shear reinforcement strain and recording the ultimate load. Each beam took about two hours to complete the test. The cracks were monitored at each load increment. Figure 4 shows the experimental set up.



Figure 4: Typical experimental set up and crack monitoring

VI. TEST RESULTS

The beam BC showed typical mode of failure by shear at the ultimate load of 180 kN. The other beams R-SSB, and N-SSB showed quite similar mode of failure. Several micro-cracks appeared early in the loading process. These cracks were extended and widened as the load increases. These cracks became visible at the load of about 100 kN. As the loading was increased more cracks developed. The cracks migrate towards the top corners as the load increases. More flexure cracks appeared at a load of 100 kN in the bending moment region. These cracks increased by increasing the applied load, and new cracks developed but at relatively slower pace. Figure 5 shows a typical mode of failure of the beam SSB (recycled and new) which is somewhat similar to the mode of failure of the other beams. In this particular beam, the shear crack area stretched from the support to a distance equals about twice the depth. The angle of the first shear crack is about 25 degrees, and propagated fast from the support toward the first applied load. This crack becomes visible at the load of 120 KN. The width and the length of this crack increases with the increase of the applied load. More cracks developed at various distances from the support. The angle of these cracks increases as the crack approaches the applied load. Some measured angles of these cracks are 40, 60 and 73 degrees. It is interesting to mention here that the bending cracks started to become visible at earlier stages of loading compared with the shear cracks. One of the main bending cracks became visible at the load level of 80 KN, and propagated slowly toward the top of the beam. This crack is located at the bottom side of the beam in the med-span area of the beam. In general, it was noticed that the width of the bending cracks is much smaller than the width of the shear cracks. Also, one can notice that the rate of crack propagation of bending cracks is much slower than the rate of propagation of the shear cracks. In general, the shear cracks moved from the support toward the mid-span propagating upward with increasing angle, while the bending cracks remained at the mid-span area and propagated vertically upward toward the top of the beam.



Figure 5: Typical failure mode of the beam reinforced with recycled spliced swimmer bars.

Figure 6 shows the maximum applied load the beam carried just before failure. All of the tested beams in this study failed by shear. Recycled splicing swimmer bars provided a practical solution to the shear problem in the reinforced concrete beams, without jeopardizing the quality or strength.

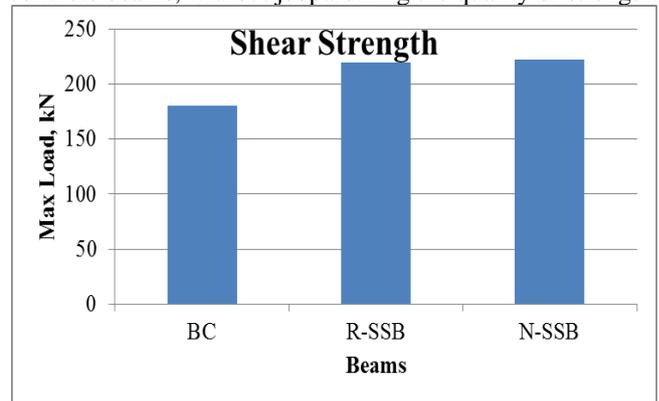


Figure 6: Shear strength of the three tested beams

Figure 7 shows the maximum measured deflection at the mid span just before the beam failure. No major difference in the load deflection relationship was observed in the tested beams. Beam deflection increases with the increase in applied load up to the failure load where the maximum deflection is recorded.

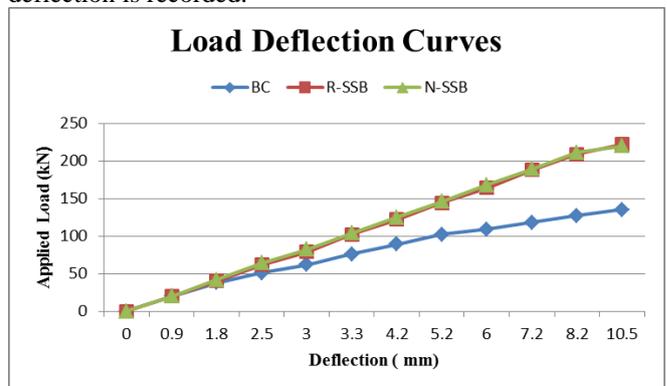


Figure 7: Maximum deflection measured at mid-span just before failure.

VII. CONCLUSION

This study presented two different types of shear reinforcement that can be used in reinforced concrete beams. New type of shear reinforcement system was used, which is the spliced swimmer bars system. New shape of swimmer bars is used and spliced with the longitudinal flexural bars. These bars are made of recycled steel reinforcement classified as Class A recycled bars. These swimmer bars formed plane-shear interceptors. In general there is improvement in shear strength of beams reinforced with swimmer bars over the beams reinforced with the traditional stirrups. The beam reinforced with recycled swimmer bars showed similar results as the beam reinforced with brand new spliced swimmer bars. The width and length of the cracks were observed to be less using swimmer bars compared to the traditional stirrups system.

ACKNOWLEDGMENT

The author would like to extend his appreciation to the Applied Science University, Amman- Jordan for sponsoring and financially supporting this research project.

REFERENCES

1. Al-Nasra, M.M., and Wang, L.R.L., 1994, Parametric Study of Slab-On-Grade Problems: Due to Initial Warping and Point Loads. *ACI Structural Journal*, Vol. 91 No. 2. <http://www.concrete.org/PUBS/JOURNALS/OLJDetails.asp?Home=SI&ID=4596>.
2. Moayyad Al-Nasra, Naeim Asha, "The Use of Bolted U—Link Swimmer Bars in the Reinforced Concrete Beams," *International Organization of Scientific Research, Journal of Engineering (IOSRJEN)*, Vol. 3 , Issue 10 , Version 5, ISSN Print: 2278-8719, ISSN Online: 2250-3021, DOI: 10.9790/3021-031052632, ANED: 0.4/3021-031052632, <http://www.iosrjen.org>, Pages 26-32, October, 2013.
3. Moayyad Al-Nasra, Naeim Asha, " Investigating the Use of Spliced Swimmer Bars as Shear Reinforcement in Reinforced Concrete Beams", , " *International Organization of Scientific Research, Journal of Engineering (IOSRJEN)*, Vol. 05 , Issue 02 , Version 02, ISSN Print: 2278-8719, ISSN Online: 2250-3021, DOI:- 05224754, ANED: 0.4/3021-05224754, ESCI-MML 3021-0502-4754, <http://www.iosrjen.org>, Pages 47-54, February 2015.
4. Piyamahant, (2002) , Shear behavior of reinforced concrete beams with small amount of web reinforcement, M. Eng. Dissertation, Kochi University of Technology, Japan.
5. Lesley H. Sneed and Julio A. 2008, Effect of Depth on the Shear Strength of Concrete Beams without Shear Reinforcement, USA Portland and cement Association. <http://www.cement.org/exec2/11-03-08.htm>
6. Noor Hamid (2005). The Use of Horizontal and Inclined Bars as Shear Reinforcement , Master Thesis, University of Technology , Malaysia, <http://sunzi.lib.hku.hk/hkuto/record/B26643352>
7. ACI 318-11, 2011. Building Code Requirements for Structural Concrete Commentary. <http://www.concrete.org/pubs/newpubs/31811.htm>
8. Edward G.Nawy, 2009. Reinforced Concrete: A Fundamental Approach, Prentice Hall International, US, PP 120-315, ISBN 0132417030, 9780132417037



Dr. Moayyad Al-Nasra is professor of civil engineering at the Applied Science University. Dr. Al-Nasra has over 60 publications including books, journal papers, and reports. Dr. Al-Nasra has about 25 years teaching experience at several universities mostly in the US.