

Variation in Heat Deflection Behaviour of Alkali Treated and Untreated Hybrid Fibre Reinforced Composites

C.M. Meenakshi, Sucharitha S, Srinivasan V



Abstract: Regular Fiber fortified composites discovers place in numerous applications as they have the benefits of being light, solid, modest and progressively ecological well disposed. This investigation planned to decide the impact of antacid treatment on normal fiber and its effect on the warmth diversion conduct of the regular and glass fiber fortified cross breed composites ,in this work two kind of half and half composite are made with glass, sisal and flax fiber ,the crossover strengthened composite covers were manufactured by hand lay-up technique. Examples are cut from the manufactured cover and their warmth diversion conduct was tried by ASTM D648 benchmarks. From the outcome it is comprehended that the basic treatment has improved the warmth avoidance withstanding limit of flax/glass half and half composite and don't have much impact on sisal/glass mixture composite.

Keyword : Alkali Treatment, Heat Deflection Behaviour, Hybrid composites, ASTM D-648.

I. INTRODUCTION

The composites are the promising materials of this century, among that various kinds of polymeric framework fortified with various materials discovered application in huge numbers of the administration businesses [1]. These days fiber Reinforced composites are broadly utilized for some, applications like auxiliary, marine, aviation, vehicle, windmill sharp edges and so forth., as a result of their high solidarity to solidness, weight to firmness proportion [2, 3]. The principle explanations behind the enthusiasm on these fortifications over manufactured fiber fortifications are their low natural effect, minimal effort, and high flexural quality, which supports their potential over a wide scope of uses [4]. Regular filaments show predominant mechanical properties, for example, adaptability, solidness and modulus contrasted with glass strands. In the ongoing days characteristic strands, for example, sisal and flax filaments are supplanting the glass

and carbon filaments attributable to their simple accessibility and cost [5]. Starting at now, various examinations have been directed by breaking down various blends of fiber and gum materials [6]. The flexural quality estimations of the half breed fiber fortified composites are sensibly great. Sisal/Glass fiber composite is performing great with the ductile burden [7]. The properties of fiber-strengthened composites rely upon numerous variables, for example, the holding between the strands and the framework, the fiber volume division, the fiber angle proportion, fiber direction and productivity of burden move at the interface [8].

Regular fiber flax is an appropriate auxiliary swap to E-glass for comparable composite little wind turbine sharp edge applications [9]. Flax strands specifically have a Young's modulus similar to glass fibres[10].whereas rigidity and solidness of flax filaments answered to be as high as 1500 MPa and 90 GPa, respectively[11]. Flax has complex inward structure that outcomes in anisotropic versatile properties. Such highlights of the strands can likewise be considered in the direction averaging approach [12]. Ductile and weariness conduct of single sisal fiber at check length GL=20 mm. Ductile cyclic weakness stacking at eight stacking levels (from 0.6 to 0.95) has been completed. The test results lead to huge reliance of the hysteresis circles, vitality scattering of the sisal strands versus the cycle and stacking proportion levels. The qualities for rd= 0.60, scattered vitality (Ed) is practically steady at an incentive around 1.2 mJ. Be that as it may, for higher level at rd= 0.95 of scattered vitality are seen around to 3.2 mJ during the primary cycle [13].Sisal fiber's warm dependability isn't influenced by dewaxing treatment while the mercerization and methyl methacrylate uniting builds the most extreme disintegration temperature by 10°C when contrasted with untreated strands [14].The elastic property of salt treated coir-polyester composite. From their outcomes it affirmed soluble base treatment gives better property and furthermore numerous scientists announced that antacid treatment expels hemicellulose and lignin viably from the cell divider. Substance treatment improves the mechanical and free vibration properties of polymer composites because of the upgrade of interfacial bond among fiber and network

Manuscript published on 30 August 2019.

* Correspondence Author (s)

CM Meenakshi, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, Tamilnadu, India.
Email: cmmeenakshidhanush@gmail.com

Sucharitha S, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, Tamilnadu, India. Email: saisuchi2002@gmail.com

Srinivasan V, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, Tamilnadu, India.
Email: nivas11@gmail.com

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](#) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

II. MATERIAL AND METHOD

Four different types of composite laminates are prepared using the following raw materials[17]:

- Epoxy resin
- Flax fibre
- Sisal fibre
- Glass fibre



Published By:

Blue Eyes Intelligence Engineering

and Sciences Publication (BEIESP)

© Copyright: All rights reserved.

In this work the sap considers is Epoxy gum (LY 556) and the hardener utilized is Araldite HY-951, the lattice is set up by blending the gum and hardener in the proportion of 10:1 and the regular filaments utilized are flax and sisal strands as biaxial mats, The glass fiber utilized is 600 Gsm biaxial glass fiber tangle.

A. Alkali Treatment

The fiber surface is treated as pursues:

1. Flax and sisal fiber tangle were washed with refined water and dried.
 2. Then the dried fiber mats were treated with 10% NaOH answer for 1hr at room temperature in a different plate.
 3. The treated fibers were washed with refined water again to expel abundance NaOH clung to the fiber tangle
 4. The washed mats were sun-dried for 8 hr and were then stove dried at 50°C for 2 hr.
- The salt treatment has been done on huge volume of flax and sisal filaments and required measure of that utilized for this work staying utilized for different works.



Figure 1- NaOH treatment of Flax and sisal Fiber

III. EXPERIMENTATION

The warmth avoidance temperature is a proportion of a composites capacity to shoulder a given burden at raised temperatures[18]. This strategy is utilized to decide the temperature at which the distortion happens when examples are exposed to characterized set of testing conditions. The component of the example were 63.0 mm × 12.8 mm × 3.2 mm (length × width × thickness).The heat redirection temperature was examined and estimated by the HDT Tester, and the rules were pursued according to the ASTM D648–01, with the stacking weight of 0.455 MPa, to the raising temperature of 2°C/min. Testing results were gotten from a normal of four examples[16].



Figure 2 - Heat deflection temperature test




IV. RESULT AND DISCUSSION


In the HDT test of the hybrid composite as well as natural fiber composite is showing almost good performance to glass fiber reinforced composite when treated with NaOH, results show that GSG (T) has slightly higher heat deflection temperature with an average of 67°C and others GFG (T), FGS (T), FGS (UT) at an average of 66.75°C, 64.6°C, 62.8°C respectively[19].

SPECIMEN NO.	GSG Treated with NaOH	GFG Treated with NaOH	FGS Treated with NaOH	FGS Untreated
1	66°C	66°C	62°C	63°C
2	68°C	67°C	66°C	64°C
3	67°C	67°C	64°C	64°C
4	67°C	67°C	65°C	61°C
5	67°C	67°C	66°C	62°C

Table-1 Results of HDT test

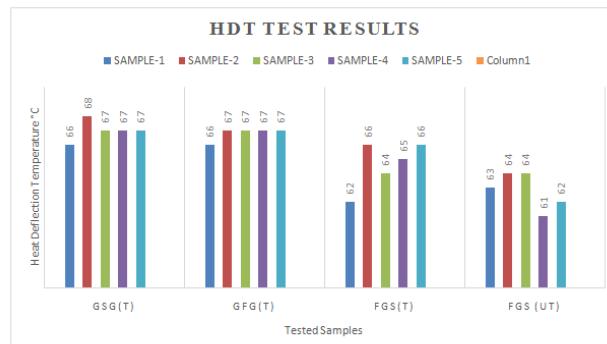

Graph-1 HDT Test Results

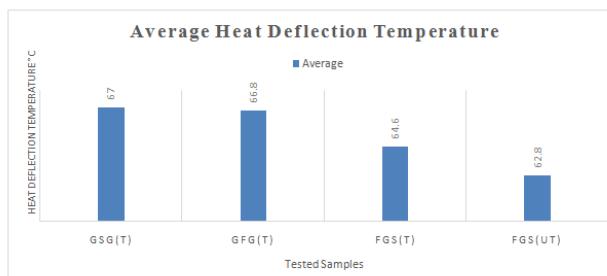

Graph-2 Average Heat Deflection Temperature

V. CONCLUSION

Thus the following conclusion drawn from the study of heat deflection behaviour.

- Fabrication of fiber reinforced laminate by hand layup method is possible
- Four types of composite laminates have been fabricated successful they are flax and glass fiber composite, sisal and glass fiber composite, flax glass and sisal (treated and Untreated with NaOH) hybrid fiber reinforced composite respectively[14].
- The above-mentioned composites are tested for their compression strength and heat deflection temperature behavior according to ASTM standards.
- Heat deflection temperature of GSG (T) is higher when compared to other three composites[15].

Further this work can be extended to by doing more comparative study between mechanical behaviour like tensile, compression strength of alkali treated and untreated natural fiber composite to understand completely about the advantages of alkali treatment on natural fibers and their influence on composite bonding strength.

REFERENCES

1. Tatikonda, N.C. & NaveenChandran, P. 2019, "The behaviour of a compression ignition engine under the influence of diesel and microalgae biodiesel blends", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 4, pp. 447-456.
2. Tatikonda, N.C. & NaveenChandran, P. 2019, "An experimental assessment on the impact of injection pressure on the characteristics of a diesel engine powered with the blend of diesel and microalgae biodiesel", International Journal of Engineering and Advanced Technology, vol. 8, no. 6, pp. 3284-3291.
3. Karthikeyan, S., Raman Balasubramanian, S.R., Ramesh, B., Raghul, S. & Sathish Kumar, S. 2019, "The automatic solar tracker chronicles", International Journal of Recent Technology and Engineering, vol. 8, no. 1, pp. 312-315.
4. Hema, R., Sundararajan, M. & Balaji, S. 2019, "Smartphone control robot with automatic firing gun", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 625-627.
5. Saritha, B., Chockalingam, M.P. & Aswathy, M. 2019, "Degradation of anionic dye using Fe/TiO₂ composite by photocatalysis", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 788-791.
6. Saritha, B., Maria Subashini, L. & Aswathy, M. 2019, "Utilization of spent coffee grounds for compost production", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 908-910.
7. Fernando, J.K., Meikandaan, T.P. & Hemapriya, M. 2019, "Better utilisation of bottom ash in coal fired thermal power station", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 898-900.
8. Kumar, K.S., Kiruthiga, K. & Thendral, S. 2019, "Experimental analysis on fractional substitution of bond by utilizing rice husk cinder", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 1163-1165.
9. Vignesh, P., Madan, P., Mohankumar, D. & NaveenChandran, P. 2019, "Optimization of four stroke c.i. engine performance by using statistical techniques (mathematical method)", International Journal of Recent Technology and Engineering, vol. 8, no. 2, pp. 1685-1691.
10. Bharanidharan, S., Sathiyamurthy, K. & Sheeba, B. 2019, "Using co-precipitation method determining synthesis and characterization of fe doped zinc oxide nanoparticles", International Journal of Innovative Technology and Exploring Engineering, vol. 8, no. 9 Special Issue 3, pp. 705-707.
11. Jeevanandan, D. & Vino, J.A. 2019, "Heat recovery from boiler blowdown water by using heat exchanger in thermal power plant", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 219-222.
12. Rakesh, N.L., Balambica, V. & Kannan, S. 2019, "Biogas extraction from waste orange peel by digestion process", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 323-330.
13. Meenakshi, C.M. & Krishnamoorthy, A. 2019, "The mechanical characterization of mono and hybrid fiber reinforced composites using experimental and finite element analysis methods", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 189-196.
14. Mohankumar, D., Prem Jayakumar, M., Sabarish, R. & Naveen Chandran, P. 2019, "Modeling and experimental investigation on centrifugal blower by computational fluid dynamics", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 331-340.
15. Balambica, V., Deepak, V. & Kumar, S. 2019, "Design and efficiency of an asymmetric gear", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 223-230.
16. Manavalan, S., Balakrishnan, G. & Ramasubramaniam, S. 2019, "An effect of cobalt oxide nano additive with biodiesel blends using cidi diesel engine", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 211-218.
17. Golden Renjith Nimal, R.J., Sivakumar, M. & Esakkimuthu, G. 2019, "An investigation on mechanical properties and microstructure of mg/al alloys using zn interlayer during diffusion bonding", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 125-130.
18. Hariharan, R., Raja, R. & Vasu, S. 2019, "Mechanical and tribological behaviour of thin tan coating produced on AISI 1018 substrate by DC magnetron sputtering", International Journal of Recent Technology and Engineering, vol. 7, no. 6, pp. 591-598
19. Manavalan, S., Rai, R., Kumar, R.R., Chaudhary, R.K. & Chaudhary, S.K. 2019, "Impact of modified piston - A review", International Journal of Recent Technology and Engineering, vol. 8, no. 6, pp. 616-620.
20. Manavalan, S., Gopi, A., Arivarasu, J., Abishek Ahi, A. & Chandru, S. 2019, "Review on ceramic disc brake system", International Journal of Recent Technology and Engineering, vol. 7, no. 6, pp. 612-615.
21. Sabarish, R. & Jeya Kumar, M.P. 2019, "The design and analysis of piston - Steady state thermal analysis using "ansys""", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 197-204.
22. Ravi, D. 2019, "CFD simulation of solar loading in car", International Journal of Mechanical and Production Engineering Research and Development, vol. 9, no. 3, pp. 231-236.

AUTHORS PROFILE



CM Meenakshi Assistant Professor, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, India.



Sucharitha S Assistant Professor, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, India.



Srinivasan V Assistant Professor, Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Chennai, India.



Published By:

Blue Eyes Intelligence Engineering

and Sciences Publication (BEIESP)

© Copyright: All rights reserved.