


Optimized Models for the Concrete using Flyash and Steel Scrap Waste By-Products



PL. Meyyappan, R. Sutharsan

Abstract: The major issue in the construction industry is to address the development of the suitable building material in a non depleting way to the environmental society. To effectively utilize the industry by-products in the construction sector will bring the cost effective solution and non polluting manner. Hence in this experimental investigation, M30 grade concrete is used in partial replacement of flyash by 0%, 10%, 20% and 30% for evaluating strength parameters. Once the optimum flyash percentage is arrived, then the steel scraps are incorporated in the percentage of 0%, 0.5%, 1%, 1.5% and 2% to enhance the strength properties further. As a result, it is profound that the optimum percentage of flyash replaced concrete is 20 % and addition of 1.5 % steel scraps is appropriate in enhancing the strength parameters. Modeling is adopted in arriving relationship for compressive strength with tensile and flexural strength for flyash replacements and addition of steel scraps. All the model equations are well correlated with the experimental results.

Keywords : Waste products, Flyash, Steel Scrap, Strength.

I. INTRODUCTION

Nowadays the construction industry faces many challenges on environment and economy aspects. In one side, the increase in cost of construction materials. This may be due to non availability and transportation cost. On the other side, the handling the waste by-products such as flyash, coal ash, steel slags, quarry dust, marble dust, steel scraps, waste glass and plastics etc. Many research works have been reported to address these challenges for a mono solution. Some of the works addressed with the utilization of these products in individual manner [Shi3, Udoeyo1, M. Mageswari5, Mannesh Joel7, K.C.Kesharwani12] or in a combined way [Ahamed8, Vasu Krishna9, M. Shahul Hameed4 , P. Aggarwal2, PL. Meyyappan13, R. Hidayawanti14]. Most of the research studies are extensively done with flyash related waste materials due to the advantage of increased workability, enhancing strength properties, resistant to acid attack etc. In order to increase the ductility and durability, fibres are added to the concrete in some studies [S.K. Ahirwar10, PL. Meyyappan13, M. Barbuta11]. But while adding fibres into the concrete, strength will be increased but construction cost will not be comes down. In order to add fibre, waste steel scraps can be better to

minimize the cost without compromising the strength parameters. Hence, an attempt is made to utilize the waste by-products into the concrete to the reasonable cost and also to handle the waste products in an utilizable approach. So, in this experimental investigation, two phases will be executed. In first, there is a study of phase flyash replaced concrete and in the second, the addition of steel scraps in the optimum flyash replaced concrete.

II. MATERIALS AND PROPERTIES

A. Cement

The Cement used in this experimental study is of OPC 53 grade conforming to IS 12269:2013. The properties of cement are given in table 1.

Table- I: Properties of Concrete Materials

S.no.	Properties	Values for		
		Cement	FA	CA
1	Specific Gravity	3.21	2.69	2.75
2	Initial Setting Time	32 mins	NA	NA
3	Final Setting Time	618 mins	NA	NA
4	Fineness Modulus	2.35 %	2.49 %	7.27 %
5	Standard consistency	31%	NA	NA
6	Bulking	NA	25 %	NA
7	Impact value	NA	NA	7.2 %
8	Abrasion value	NA	NA	19.4 %
9	Crushing value	NA	NA	19.8 %

B. Fine Aggregate (FA)

The naturally available river sand having glossy texture and round in shape is used as fine aggregate conforming to requirements of zone II as per IS:383-1970. Fine aggregate passing through 4.75mm sieve is considered for this study and its properties are given in table 1.

C. Coarse Aggregate (CA)

The natural rock aggregates having angular and irregular texture passing to 20 mm sieve and retained on 4.75 mm sieve is used in this study. The properties of coarse aggregate are as given below in table 1.

D. Flyash

Flyash of class C category obtained from Tuticorin thermal power plant, Tamil Nadu is used in this study. The flyash passing through 90 micron sieve is used as the replacement material of cement. Thereby, the conventional usage of cement can be minimized.

E. Steel scrap

Steel scrap is a waste product from lathe industries. The average dimensions are 1 mm in diameter and 10 mm in length is used in this work. Its nature is a twisted type.

Manuscript published on 30 December 2019.

* Correspondence Author (s)

PL. Meyyappan*, Civil department, Kalasalingam Academy of Research and Education, Krishnankoil, India. Email: meyyappan@klu.ac.in
R. Sutharsan, Civil department, Kalasalingam Academy of Research and Education, Krishnankoil, India. Email: r.sutharsan@klu.ac.in

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](https://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

F. Water

Portable drinking water is used in this experimental work.

III. MIX DESIGN AND INVESTIGATIONS

In this experimental investigation, M30 grade concrete is used. The design mix proportion arrived as per IS10262:2009 is 1: 1.46: 2.43 with a W/c ratio of 0.45. The experimental investigation is planned and executed in two phases. In first phase, properties of flyash replaced concrete and in the second phase flyash and steel scrap blended concrete are investigated. In this first phase, the cement is partially replaced by flyash in different percentages namely 0 %, 10 % 20 % and 30 %. For each replacement of flyash percentage, 12 cubes of size 150 mm x 150 mm x 150 mm, 12 cylinders of size 300 mm x 150 mm and 12 prisms of size 500 mm x 100 mm x 100 mm were cast to test compressive strength, split tensile strength and flexural strength test respectively.

In the second phase, steel scrap of different percentages from 0 %, 0.5 %, 1.0 %, 1.5 % and 2.0 % are added to the total volume of the optimum percentage of flyash replacement on the concrete which is arrived at the first phase. In the second phase, steel scrap is added to the optimum percentage of flyash replaced concrete arrived at the first phase. For each addition of steel scrap percentage, 15 cubes of size 150 mm x 150 mm x 150 mm, 15 cylinders of size 300 mm x 150 mm and 15 prisms of size 500 mm x 100 mm x 100 mm were cast to test compressive strength, split tensile strength and flexural strength test respectively. All the tests were carried out in the universal testing machine with a capacity of 2000 kN. Out of 81 specimens, 36 specimens and 45 specimens were casted, cured in water and tested for 28 days for first phase and second phase respectively.

IV. EXPERIMENTAL RESULTS AND DISCUSSIONS

A. Flyash replaced concrete

Table 2 shows the compressive strength, split tensile strength and flexural strength test results of a flyash replaced concrete in the proportions of 0%, 10%, 20% and 30%. The maximum compressive strength of 34.12 N/mm² is attained at the flyash replacement of 20 % for the age of 28 days. Simultaneously at this replacement proportion, the maximum split tensile strength and maximum flexural strength is attained as 1.96 N/mm² and 5.88 N/mm² respectively. From figures 1 to 3, it is clearly understood that if flyash replacement is increased strength also get increased because the flyash is very fine particles and fill the pores in the concrete by making the concrete highly dense. Beyond 20 % of flyash replacement, the various strength properties tends to decrease may due to the limiting binding property of cement. By replacing cement to flyash upto 20 %, the compressive strength increases 15.34 %, split tensile strength increases 17.8 % and flexural strength increases 34 % when compared with 0% of flyash replacement. Thereby the test results clearly indicating the replacement of flyash that the optimum flyash replacement is found to be 20 %.

B. 4.2 Flyash and Steel scrap blended concrete

In the second phase, the different percentages of steel scraps viz. 0%, 0.5%, 1%, 1.5% and 2% are added on the optimum 20 % flyash replacement proportion which is found

on the first phase of the study and the test results of compressive strength, split tensile strength and flexural strength of the flyash and steel scrap blended concrete are tabulated in table 3.

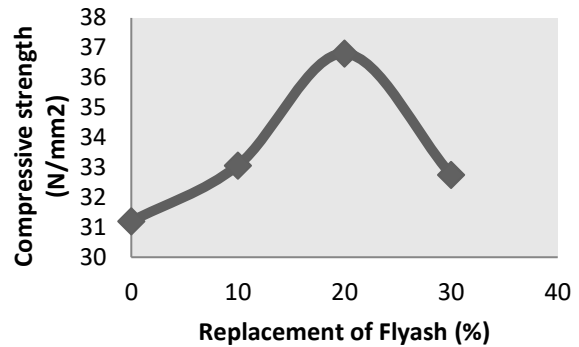


Fig. 1. Compressive strength Vs Flyash replacement.

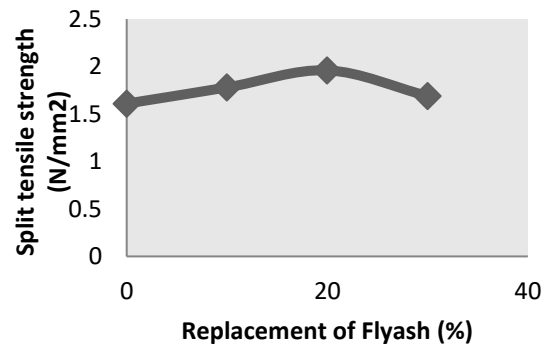


Fig. 2. Split tensile strength Vs Flyash replacement

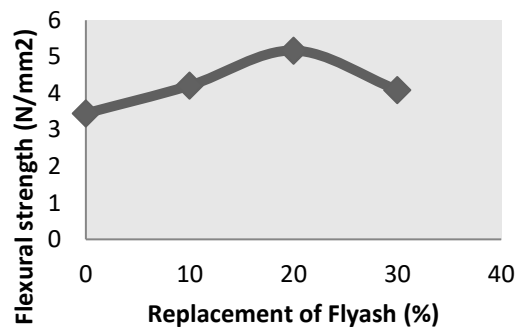


Fig. 3. Split tensile strength Vs Flyash replacement

By the addition of steel scraps upto 1.5% on the flyash replaced concrete, the compressive strength increases to 37.91 N/mm² from 33.81 N/mm². Simultaneously the split tensile strength and flexural strength increases to 2.35 N/mm² from 1.93 N/mm² and 6.47 N/mm² from 5.61 N/mm² respectively. From figures 4 to 6, it is clearly understood that strength properties gets declined when addition of steel scraps increased from 1.5% to 2%.

It seems that, the addition of steel fibres upto 1.5% on the optimum 20% flyash replaced proportion is advantages in enhancing strength properties and maintains proportionality.

This steel scraps occupied the micro-pores of the concrete and thereby preventing the crack propagation process and adding toughness to the concrete. By adding optimum flyash replacement of 20 % and steel scraps of 1.5 %, the

compressive strength increased to 18%, split tensile strength increased to 32% and flexural strength increased to 45%. Thereby the test results clearly indicating that the utilization of waste by products flyash and steel scraps plays a vital role in enhancing the mechanical properties of the concrete in an optimum proportion.

Table- II: Test results for flyash replaced concrete

S.No	Specimen	Cement (%)	Flyash (%)	Compressive Strength (N/mm ²)	Split Tensile Strength (N/mm ²)	Flexural Strength (N/mm ²)
1	FA 0	100	0	31.2	1.61	3.45
2	FA 10	90	10	33.07	1.78	4.21
3	FA 20	80	20	36.81	1.96	5.17
4	FA 30	70	30	32.76	1.69	4.09

Table- III: Test results for flyash and steel scrap blended concrete

S.No	Specimen	Cement (%)	Flyash (%)	Steel Scrap (%)	Compressive Strength (N/mm ²)	Split Tensile Strength (N/mm ²)	Flexural Strength (N/mm ²)
1	FAS 0	80	20	0	33.88	1.93	5.61
2	FAS 0.5	80	20	0.5	34.89	1.99	5.85
3	FAS 1.0	80	20	1.0	36.28	2.23	6.19
4	FAS 1.5	80	20	1.5	37.91	2.35	6.47
5	FAS 2.0	80	20	2.0	34.19	1.98	5.82

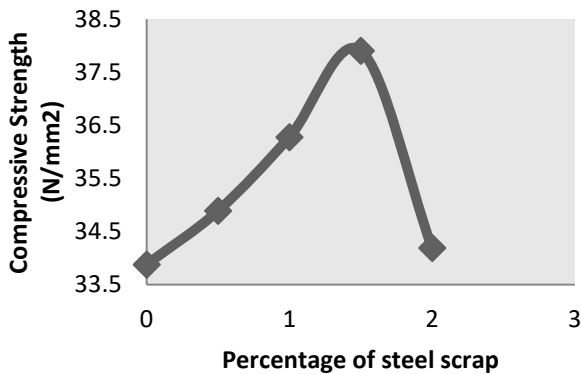


Fig. 4. Compressive strength Vs Percentage of steel scrap

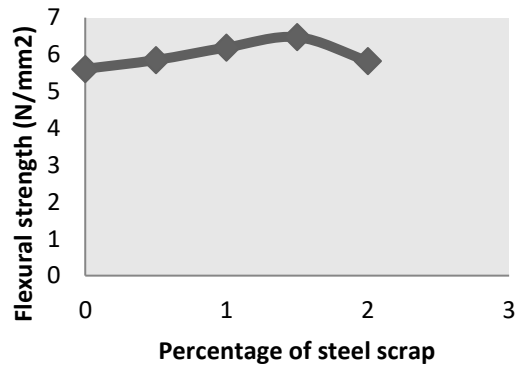


Fig. 6. Flexural strength Vs Percentage of steel scrap

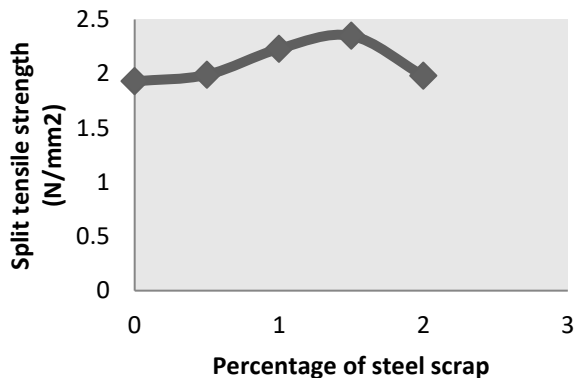


Fig. 5. Split tensile strength Vs Percentage of steel scrap

V. MODELLING APPROACH AND DISCUSSIONS

A. Relating strength Properties Vs Flyash

Equations based on regression analysis are arrived in this study based on the experimental data to validate. Table 4 shows the various types of model equations such as exponential, linear, polynomial 2d and 3d and their validity levels for relating flyash replacement levels (Fa) with compressive strength (Cs), split tensile strength (Ts) and flexural strength (Fs) respectively.

Table- IV: Model equations relating strength parameters and flyash replacement

Model Equation	Equation Type	Validity
$C_s = 32.15 e^{0.005 F_a}$ $T_s = 1.692 e^{0.002 F_a}$ $F_s = 3.76e^{0.007 F_a}$	Exponential	Valid for flyash replacement of 10%
$C_s = 0.084 F_a + 32.19$ $T_s = 0.004 F_a + 1.697$ $F_s = 0.028 F_a + 3.798$	Linear	Valid for flyash replacement of 10%
$C_s = -0.014 F_a^2 + 0.528 F_a + 30.71$ $T_s = -0.001 F_a^2 + 0.037 F_a + 1.587$ $F_s = -0.004 F_a^2 + 0.166 F_a + 3.338$	Polynomial (2d)	Valid for flyash replacement of 20%
$C_s = -0.001 F_a^3 + 0.057 F_a^2 - 0.228 F_a + 31.2$ $T_s = -0.008 F_a^3 + 0.002 F_a^2 - 0.001 F_a + 1.61$ $F_s = -0.005 F_a^3 + 0.012 F_a^2 - 0.008 F_a + 3.45$	Polynomial (3d)	Valid for flyash replacement of 20%

Table- V: Model equations relating strength parameters and steel scraps

Model Equation	Equation Type	Validity
$C_s = 34.69 e^{0.020 S_s}$ $T_s = 0.728 e^{0.043 S_s}$ $F_s = 5.775 e^{0.034 S_s}$	Exponential	Valid for addition of steel scraps 0.5% to 1 %
$C_s = 0.728 S_s + 34.70$ $T_s = 0.092 S_s + 2.004$ $F_s = 0.208 S_s + 5.78$	Linear	Valid for addition of steel scraps 0.5% to 1 %
$C_s = -2.634 S_s^2 + 5.996 S_s + 33.38$ $T_s = -0.28 S_s^2 + 0.652 S_s + 1.864$ $F_s = -0.525 S_s^2 + 1.259 S_s + 5.517$	Polynomial (2d)	Valid for addition of steel scraps 0.5% to 1.5 %
$C_s = -3.82 S_s^3 + 8.825 S_s^2 - 2.216 S_s + 33.95$ $T_s = -0.446 S_s^3 + 1.06 S_s^2 - 0.308 S_s + 1.931$ $F_s = -0.686 S_s^3 + 1.534 S_s^2 - 0.216 S_s + 5.620$	Polynomial (3d)	Valid for addition of steel scraps 0.5% to 1.5 %

$$F_s = 1.05 \sqrt{C_s} \tag{4}$$

B. Relating strength Properties Vs Steel scraps

Table 5 shows the various types of model equations such as exponential, linear, polynomial 2d and 3d and their validity levels for relating addition of steel scraps (Ss) with compressive strength (Cs), split tensile strength (Ts) and flexural strength (Fs) respectively. From table 4 and 5, model equations represents in a simple and complex way with various model types. Among those types of models polynomial equation (2d & 3d) suits better for up to 20 % of flyash replacement and 1.5 % steel scraps proportion. For lower (up to 10%) proportion of replacement of flyash and (up to 1.5%) addition of steel scraps, the other model types, namely exponential and linear equations performs in a better way in correlation with the experimental results.

C. Relating all strength properties

Based on the experimental test results, the equation 1 and 2 represents the relation of compressive strength with split tensile strength and flexural strength respectively for the flyash replacement proportions. The equation 1 and 2 will be valid for the flyash replacement level up to 20 % and the results in correlation in the range of ± 10%.

$$T_s = 0.32 \sqrt{C_s} \tag{1}$$

$$F_s = 0.38 \sqrt{C_s} \tag{2}$$

Similarly 3 and 4 represents the relation of compressive strength with split tensile strength and flexural strength respectively for the addition of steel scraps. The equation 3 and 4 will be valid for the addition of steel scraps up to 1.5 % and the results in correlation in the range of ± 12.5%.

$$T_s = 0.85 \sqrt{C_s} \tag{3}$$

VI. CONCLUSION

The following conclusions are arrived based on this experimental study:

1. Utilization of flyash and steel scraps addressed the two major issues such as disposal of waste by-products and limiting the cost of construction.
2. The Co2 emission rate can be reduced based on the utilization of waste by-products flyash and steel scraps and thereby the usage of cement content on the concrete can be limited.
3. The optimum flyash replacement was found to be 20 %, since there is an increase of 15 % in compressive strength, 18% in split tensile strength and 34% in flexural strength.
4. Further, if steel scraps of 1.5% (optimum) on the 20 % flyash replacement level, the compressive strength, split tensile strength and flexural strength increased by 18%, 32% and 45% respectively.
5. Various types of model equations such as exponential, linear, polynomial 2d and 3d are arrived. Relations of compressive strength with split tensile strength and flexural strength was found for flyash replaced concrete and flyash steel scrap blended concrete. The equations are well correlated in the range of ± 10% to ± 12.5%.

REFERENCES

1. Udoeyo F.F., Inyang H., Young T.D., Oparadu E.E (2006), "Potential of wood waste ash as an additive in Concrete.", ASCE-Journal of Materials in Civil Engineering, Vol. 18, No 4.
2. P. Aggarwal, Y. Aggarwal, S.M. Gupta (2007), "Effect of Bottom Ash as Replacement of Fine Aggregates in Concrete, Asian Journal of Civil Engineering (Building And Housing) Vol. 8, (1).
3. Shi C. (2009), "Corrosion of glasses and waste mechanism of concrete containing waste glasses as Aggregates." ASCE-Journal of Materials in Civil Engineering, Vol. 21. No 10.
4. M. Shahul Hameed, A. S. S. Sekar (2009), "Properties of Green Concrete Containing Quarry Rock Dust and Marble Sludge Powder as Fine Aggregate", ARPN Journal of Engineering and Applied Sciences, Vol. 4(4).
5. M. Mageswari, B.Vidivelli (2010), "The Use of Sheet Glass Powder as Fine Aggregate Replacement in Concrete", The Open Civil Engineering Journal, Vol 4.
6. Veera Reddy. M (2010), "Investigations on stone dust and ceramic scrap as aggregate replacement in concrete", International Journal of Civil And Structural Engineering, Vol 1(3).
7. Mannesh Joel (2010), "Use of Crushed Granite Fine as Replacement to River Sand in Concrete Production", Leonardo Electronic Journal of Practices and Technologies, Vol 9(17).
8. Ahmad S.F.U (2012), "Properties of concrete containing construction and demolition wastes and fly ash.", ASCE-Journal of Material in Civil Engineering, Vol. 1.
9. Vasu Krishna, G.M. Sabnis (2013), "Utilization of Waste Products and By-Products in Concrete: The Key to a Sustainable Construction", International Conference on Civil and Architecture Engineering (ICCAE'2013), Malaysia.
10. S.K. Ahirwar, K. Chandraul, M.K. Singh (2017), "Experimental study on concrete using flyash and coconut coir fibre", International Research Journal of Engineering and Technology, Vol.4 (6).
11. M.Barbuta, A.A. Serbanoiu (2017), "Combined effect of flyash and fibers on properties of cement concrete", Procedia, Vol. 181.
12. K.C.Kesharwani, A.K. Biswas (2017), "Experimental study on use of flyash in concrete", International Research Journal of Engineering and Technology, Vol.4 (9).
13. PL. Meyyappan, K.Kumaran, M. Gopalakrishnan and E. Harikrishnan (2018), "Effect of glass fibers, flyash and quarry dust on strength and durability aspects of concrete – An Experimental study", IOP Conference series, Material Science and Engineering, Doi 10.1088.
14. R. Hidayawanti, S. Legino, D. Harjanto (2018), "Optimizing the utilization cement slag and flyash of concrete quality", International journal of advances in mechanical and civil Engineering, Vol. 5 (2).
15. PL. Meyyappan, K.Kumaran, M.Gopalakrishnan and E. Harikrishnan (2018), "Experimental Investigation on the Effect of Silica fume and Pumice stone in Developing Light Weight Concrete", IOP Conference Series: Material Science and Engineering, doi:10.1088/1757-899X/561/1/012064.
16. PL. Meyyappan, P. Amuthakannan, R. Sutharsan and M. Ahamed Azik Ali (2019), "Utilization of M-Sand & Basalt Fiber in Concrete: An Experimental Study on Strength and Durability Properties", IOP Conference Series: Material Science and Engineering, doi:10.1088/1757-899X/561/1/012035.

AUTHORS PROFILE



Dr. PL. Meyyappan has completed his graduation and post-graduation from Bharathiyar University and Karunya University respectively. He completed his PhD from Kalasalingam University. He has 13 years of teaching experience. He has completed 2 sponsored research projects from TNSCST and published more than 25 papers in peer reviewed journals and conferences. He is a life member in ISTE, IEI, IGS, ISET, ISRS. He is serving as Editorial Board Member and Reviewer in various reputed Journals.



Mr. R. Sutharsan completed his M.E in Structural Engineering in Thiagarajar College of Engineering, Madurai in the year 2016. He completed his Bachelor of Engineering under Anna University in the year 2013. He is working as Assistant Professor in Department of Civil Engineering at Kalasalingam University, Tamilnadu, India.

His main thrust research areas is Fiber reinforced concrete.