

Influence of Activator on the strength of Ultra Fine Natural Steatite Powder based on Geopolymer Mortar



Premkumar R, Ramesh Babu Chokkalingam, M Shanmugasundaram

Abstract: In this study the detailed analysis was made on alkali activated ultra fine natural steatite powder (UFNSP) mortars. The activating alkali was prepared through sodium hydroxide and sodium silicate with different molarities concentration of NaOH. The molarities of NaOH are various from 8, 10, 12, 14 and 16. The proportion of sodium hydroxide and sodium silicate proportion are fixed 1:2.5. Further the strength gained was accelerated through polyvinyl alcohol [PVA]. And various water binder ratio of 0.5, 0.6, 0.7, 0.8 and 0.9 with addition of PVA. For workability purpose super plasticizer was used, here Poly carboxylic ether was used as a superplasticizer. These various ratios concentration of alkali activators were tried on compressive strength of polymer mortar and the results were discussed. The watched outcomes demonstrate that, increment in sodium hydroxide content in soluble base fluid expands the strength. Exhibit the outcome was effect of Si/Al proportion on compressive strength of the specimen with various water binder proportions. In general, the study shows that integrating low ratio of Si/Al content in UFNSP with PVA can fetch low binding property on alkali activator UFNSP material.

Keywords: Mortar strength, PVA, Si/Al ratio, Steatite Powder.

I. INTRODUCTION

Geopolymers have developed as a new development designing materials with the possibility to frame another component of an ecologically maintainable development and building items. These geopolymers have a low greenhouse impression when contrasted with preservationist bond concrete. Alkali activator type and its fixation assume the most significant job in the quality of geopolymers [1]. So as to guarantee practical advancement, specialists all around the globe have concentrated their examination on supplanting and reusing waste materials to supplant normal materials. Dr. K. Sudalaimani and Dr. M. Shanmugasundaram. [2] Determined about the cement setting time and pozzolanic activity and also they did UFNSP replacement of 5%, 10%,

15%, 20%, 25% with mass of cement and tested using XRD, SEM analysis, also studied micro structural behavior, chemical element distribution. Found that the dormant period shortened, initial and final setting time reduced. Compressive strength, consistency of binding material for C5, C10, C15 was also studied. It shows denser micro structural bond in C15 and denser hydration product in C20 and micro structural similarity in C25 showed disintegrated micro structure, low density. It is concluded that utilization with cement component not more than 20%. They concluded percentage should not exceed 20%. De Molcon's Recueil Industriel [3] Determined Specific gravity of steatite as 2.60 to 2.66, used more common in Germany and in Cornwall, western parts of France. Mixture of silex, alumine, magnesia, oxide of iron and water gave more durability and it did not affect colours. When it was combined with oil or grease, it goes into creation of larger pieces of balls and when blended with oil it was utilized to clean glass and metallic mirrors. M. Palacios [4] told except naphthalene based product, the product lost fluidity property. A mortar activated with NaOH act as shrinkage reducing admixtures and decrease surface tension, lowers capillary tension and furthermore diminished shrinkage during vanishing of water. Sodium lignosulphonate and naphthalene reduces compressive strength without improving workability but when naphthalene used with NaOH not altered formulation but gave rise in mechanical strength [5].

II. MATERIALS

A. Steatite Powder (UFNSP)

Steatite is otherwise called soapstone, which is a kind of transformative shale and has a lot of mineral powder. It is wealthy in magnesium. It is produced by dynamo-thermal metamorphism, which occurs in the zones where tectonic plates are sub ducted. Steatite is the softest material than all other minerals which is rated as one on mohs hardness scale. Chemical properties of steatite powder were SiO₂ - 62.67%, Al₂O₃ - 0.24%, MgO - 33.26%, Fe₂O₃ - 0.30%, CaO - 0.20%. There is no fixed hardness for soapstone because the amount of talc varies in it. Steatite is a softest material.

B. Alkaline Solution

Sodium silicate and sodium hydroxide are used to make alkali activated solution. The soluble base utilized was comprised of a blend of NaOH and Na₂SiO₃ arrangement. A NaOH solids piece must be liquefied in refined water to make a solution with the required concentration.

Manuscript published on 30 December 2019.

* Correspondence Author (s)

Premkumar R*, School of Environmental and Construction Technology, Department of Civil Engineering, Kalasalingam Academy of Research and Education, Krishnan Koil, Tamil Nadu, India. Email: prem.ce@gmail.com

Ramesh Babu Chokkalingam, School of Environmental and Construction Technology, Department of Civil Engineering, Kalasalingam Academy of Research and Education, Krishnan Koil, Tamil Nadu, India. Email: babussr@gmail.com

M Shanmugasundaram, School of Mechanical and Building Sciences, Vellore Institute of Technology, Chennai, Tamil Nadu, India, shanmugaresearch@gmail.com

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an open access article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>



In this investigation, different molarities of sodium hydroxide concentration were used to manufacture various specimens. For instance 400 grams of sodium hydroxide in drop structure is broken down in 1 liter of impartial water to make 10Molarity arrangement. NaOH and Na₂SiO₃ were mixed in the fixed ratio of 1:2.5 [6] and this liquid is used for the preparation of specimens.

C. Superplasticizer

In this study has used superplasticizer as Poly carboxylic ether with low dosage of 0.2% by weight of binding materials. Its allow water reduction up to 40% which enables good particle dispersion and composed by methoxy poly ethylene glycol co-polymer, grafted with methacrylic acid co-polymer. It grants adsorption on the emphatically charged colloidal particles. This displacement of polymer on particle surface ensures the possibility to exert repulsion forces which disperse the particles of suspension and avoid friction.

D. Polyvinyl Alcohol (PVA)

PVA is a manufactured polymer with the equation [CH₂CH(OH)]_n. It is used as an emulsion polymerization aid, and it makes dispersion of polyvinyl acetate, as protective colloid. It has a softening purpose of 230°C for completely hydrolyzed and for in part hydrolyzed evaluation it is 180-190°C. Poisson's proportion is somewhere in the range of 0.42 and 0.48.

E. Fine Aggregate

Aggregate are utilized for financial condition. What's

more, it is utilized as filler and it don't respond with cement mortal. The advancement of hard bond quality between aggregate particles and cement glue relies superficially surface, surface harshness and porosity of aggregate. Using fine aggregate was conforming to Zone II of IS 383-1970 having specific gravity 2.63 and fineness modulus 3.10. Water absorption and bulk density were 0.85% and 1.25kg/m³

III. METHODS AND CASTING

A. Mix Proportion

Sums oftwently blends were made to examination the impact of different centralizations of NaOH solids with various activator binder proportions on compressive strength. The details of these mixtures are showing in table I. The aggregate binder mixes kept constant ratio of 1:3 for all mix proportion. The mortar paste mix proportion of components was considered based on the absolute volume method. In this test work, geopolymer mortar was set up with five unique molarities of sodium hydroxide arrangements i.e; 8M, 10M, 12M, 14M and 16M. The heaviness of atomic sodium hydroxide is 40gm. sodium hydroxide is set up by dissolving pellets in water. The mass of NaOH differed relying upon the centralization of arrangement. Proportion of sodium hydroxide to sodium silicate utilized in this ratio is 2.5[7]. Table II shows required solid content was measured with corresponding molarities [8]

Table- I: Mix Proportion

S.No	NaOH	NaOH g/l	Na ₂ siO ₃ g/l	UFNSP kg/m ³	Sand kg/m ³	Naoh / Binding	W/B Ratio	PVA
1	320	262	655	750	2250	0.35	0.5	1%
2	400	312	780	750	2250	0.42	0.5	1%
3	480	362	905	750	2250	0.48	0.5	1%
4	560	404	1010	750	2250	0.54	0.5	1%
5	640	444	1110	750	2250	0.59	0.5	1%
6	320	262	655	750	2250	0.35	0.6	1%
7	400	312	780	750	2250	0.42	0.6	1%
8	480	362	905	750	2250	0.48	0.6	1%
9	560	404	1010	750	2250	0.54	0.6	1%
10	640	444	1110	750	2250	0.59	0.6	1%
11	320	262	655	750	2250	0.35	0.7	1%
12	400	312	780	750	2250	0.42	0.7	1%
13	480	362	905	750	2250	0.48	0.7	1%
14	560	404	1010	750	2250	0.54	0.7	1%
15	640	444	1110	750	2250	0.59	0.7	1%
16	320	262	655	750	2250	0.35	0.8	1%
17	400	312	780	750	2250	0.42	0.8	1%
18	480	362	905	750	2250	0.48	0.8	1%
19	560	404	1010	750	2250	0.54	0.8	1%
20	640	444	1110	750	2250	0.59	0.8	1%

Table- II: Section Properties of Castellated Beam

S.No	Molarities	Weight Solid in NaOH grams
1	8	262
2	10	312
3	12	362
4	14	404
5	16	444

B. Casting and Curing

The mixing of UFNSP with fine aggregate was dry mixed in the one to two minutes then PVA is added and mixed for one minute. Then super plasticizer and alkaline solution were added right away to the dry mix. The mixing methodology continued with the objective that absolutely homogeneous glue can be got. At that point, the acquired geopolymer mortar were filled the cube moulds 100mm x 100mm x 100mm before being totally inflexible, and after 24h they were expelled from the form and relieved at a temperature 70°C in oven for a period of 48hours. After the specimens were kept in room temperature and measured compressive strength after 28 days



Fig. 1. Casting of Geopolymer Mortar



Fig. 2. Curing of Mortar Cube

IV. RESULT AND DISCUSSION

A. Compressive Strength

The estimations of normal compressive strength and standard deviation for mortar cube shapes in proportion 1:3 for various molarities were appeared in figures 3 to 7. The compressive strength of geopolymer mortar is usually viewed as its most significant trademark. The test results of twenty mix proportion were presented in the figures 3 to 7. All the mix proportion results were compared with known value of 43MPa in 48h (Davidovits). The M8 mix proportion with W/B ratio 0.7 achieves only 51% of the total required strength geopolymer mortar cube and addition of W/B ratio decline the strength. The M10 specimen has an average compressive strength of 24.84MPa which is 56% of strength to be attainment of objective value on W/B ratio 0.7. But the strength of M10 value is greater than M8. As can be found from investigation the effect of W/B ratio increase 0.5 to 0.9, initially increase the compressive strength of the mortar further decline the strength and workability of specimens. The M12 shows the average compressive strength of 27.37MPa and M14 shows average compressive strength of 32.7MPa at the water binder ratio 0.7. The M14 has almost achieve the nominal strength of PPC cement mortar was attained. The compressive strength of M16 was periphery increase with respect to W/B ratio.

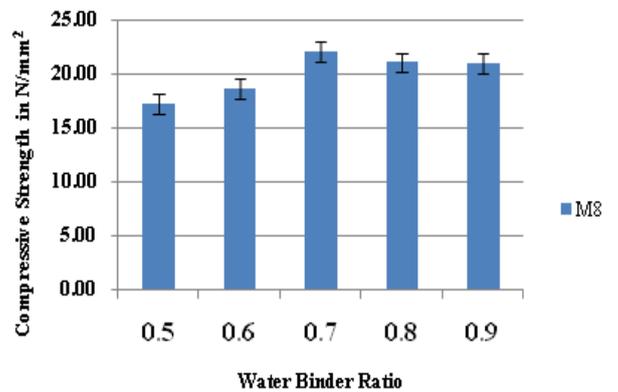


Fig. 3. Effect of Water Binder Ratio on Compressive Strength of M8

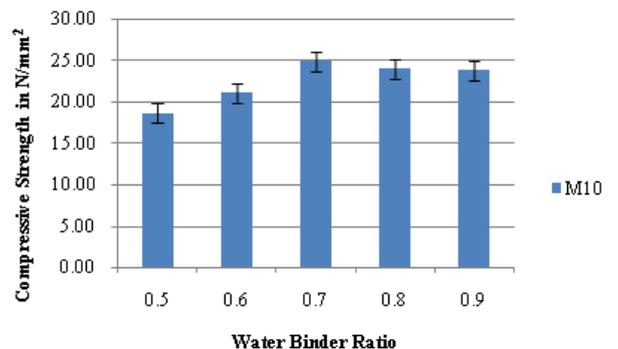


Fig. 4. Effect of Water Binder Ratio on Compressive Strength of M10

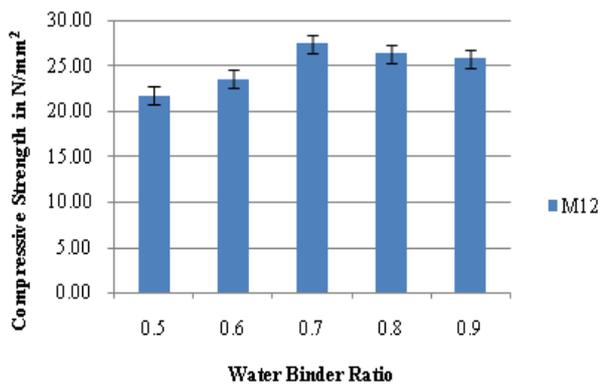


Fig. 5. Effect of Water Binder Ratio on Compressive Strength of M12

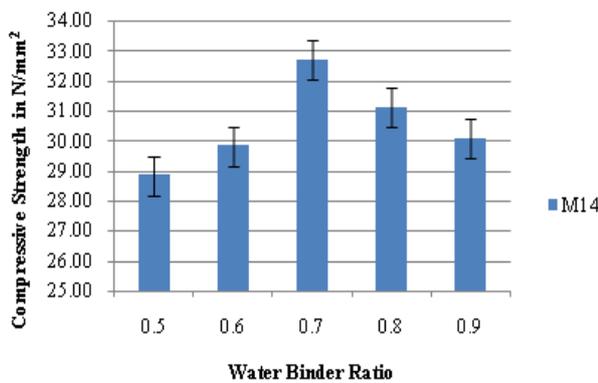


Fig. 6. Effect of Water Binder Ratio on Compressive Strength of M14

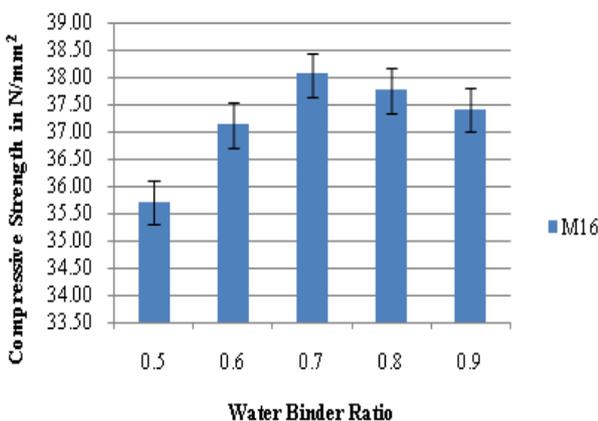


Fig. 7. Effect of Water Binder Ratio on Compressive Strength of M16

B. Effect of NaOH Binder Ratio

Mix proportions of geopolymer mortars (relate to 0.35, 0.42, 0.48, 0.54 and 0.59 individually) were set up to investigate the impact of water to binder proportion on the compressive quality of the geopolymer mortar. Figure 8 outlines the impact of water to strong proportion on the compressive quality. As it was unsurprising developing the water to strong proportion diminished the 28 days compressive strength; however, as it can be observed the

ratios of NaOH to binder and water binder ratio another way influence the compressive strength of geopolymer mortars. As preserve be establish from Figures 6, the effect of water binder ratio is unbalanced, however, the compressive strength is growing with the increment of NaOH binder ratio. As shown in figure 8 compressive strength of the geopolymer mortar increases with solid content of sodium hydroxide to binder ratio increasing from 0.35 to 0.59, whereas there is an decreasing tendency in compressive strength with water / binder ratio rising from 0.5 to 0.9 [9]. At steady activator to binder ratio and lime extent, expanding solid to binder proportion means expanding molarity of activator, and different specialists found that the molarity of basic arrangement affects the quality of geopolymer binder [10],[11].

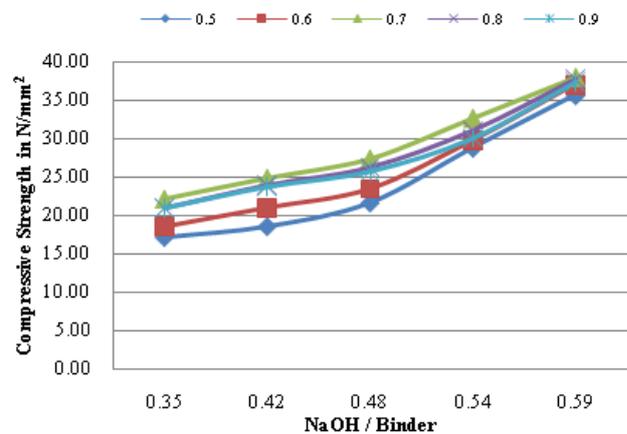


Fig. 8. Effect of NaOH / Binder ratio with Water Binder Ratio

V. CONCLUSION

- Higher the NaOH fixation higher the strength was observed, which demonstrates that no delaying alkaline is formed even in 16 Molarity.
- With the water binder proportion expanding from 0.5 to 0.9, compressive strength of the mortar builds first, and after that diminishes. The water / binder ratio also affects the compressive strength of geopolymer mortars.
- It is comprehended that higher water binder proportion will prompt lower compressive strength because of the vanishing of free water atoms as affirmed result investigation.
- It very well may be deduced that the more Si/Al proportion geopolymer mixers profit by, the higher strength can be normal.
- From all of the results it will in common be considered that the alkaline solution nearby steatite powder can go about as binder, the objective strength improvement in this alkali activated steatite based binder couldn't be accomplished by expanding NaOH solid substance and water binder proportion of geopolymer mortar.

REFERENCES

1. Connie Ng, U. Johnson Alengaram, Leong Sing Wong, Kim Hung M, MohdZaminJumaat, and S. Ramesh, "A review on microstructural study and compressive strength of geopolymers mortar, paste and concrete", *Construction and Building Materials*, vol.186, pp. 550–576, 2018.
2. Sudalaimani. K and Shanmugasundaram. M, "Influence of Ultrafine Natural Steatite Powder on setting time and Strength Development of Cement", *Advances in Materials Science and Engineering*, vol. 2014, Article ID 532746, 2014. Available from: <http://dx.doi.org/10.1155/2014/532746>
3. De Molcon'sRecueilIndustriel, "on the uses of steatite; and particularly in the lubrication of ma-chinery to reduce friction" *Journal of the Franklin Institute*, 5 (1830)
4. M.Palacios, F.Puertas, "Effect of Super Plasticizer and Shrinkage Reducing Admixtures on Alkali Activated Slag Pastes and Mortars", *Cement and Concrete Research*, vol. 35(7), pp1358-1367, 2004, DOI: 10.1016/j.cemconres.2004.10.014
5. Dr. S. G. Shah Parth, D. Parikh Harshvardhan, S. Mehta Vishal and R. Trivedi, "A Study on Effect of Curing Condition & Molarity Concentration on Geo-polymer Concrete", *Indian Journal Of Applied Research*, vol.5(1),pp. 60 – 63, 2015
6. Shanmugasundaram M, Premkumar R, Abinaya, Arunya KG, Gowsalya M and Malathy M, "A new cement free binding material based on steatite powder activated through alkaline solution" *Master Builder*, vol 18(3),pp. 60 -64, 2016
7. R Premkumar, Ramesh Babu Chokkalingam and M Shanmugasundaram, "Durability Performance of Fly Ash and Steatite Powder Based Geopolymer Concrete", *IOP Conference Series: Materials Science and Engineering*, vol. 561, 012055, 2019, Available from: <https://doi.org/10.1088/1757-899X/561/1/012055>
8. Robina Kouser Tabassum, Ankush Khadwal, "Effect of Sodium Hydroxide Concentration on Various Properties of Geopolymer Concrete", *International Journal of Engineering and Technical Research (IJETR)*, vol. 3(10), pp.454-4698, 2015
9. Andi Arham Adam, Bayu Rahmat Ramadhan, and Shyama Maricar, "The Effects of Water to Solid Ratio, Activator to Binder Ratio, and Lime Proportion on the Compressive Strength of Ambient-Cured Geopolymer Concrete", *Journal of the Civil Engineering Forum*, vol.5(2), pp.161-168, 2019, Available from: <https://doi.org/10.22146/jcef.43878>
10. Keun-Hyeok Yang, Hey-Zoo Hwang, and Seol Lee, "Effects of Water-Binder Ratio and Fine Aggregate–Total Aggregate Ratio on the Properties of Hwangtoh-Based Alkali-Activated Concrete", *J. Mater. Civ. Eng.*, vol.22(9), pp.887-896, 2010, Available from: DOI: 10.1061/ASCE MT.1943-5533.0000091.
11. Zhang P, Zheng Y, Wang K, Zhang J, A review on properties of fresh and hardened geopolymer mortar, *Composites Part B (2018)*, Available from: Doi: 10.1016/j.compositesb.2018.06.031

patents. He has 3 years of industrial experience and 10 years of teaching experience. His recent research interests include, sustainable materials and polymer concrete.

AUTHORS PROFILE



R.Premkumar had completed B.E degree in Civil Engineering and M.E degree in Structural Engineering from Anna University, Chennai, Tamil Nadu in 2008 and 2012 respectively. He is currently working as Assistant Professor in the department of Civil Engineering at Kalasalingam Academy of Research and Education. He has 2 year of industrial experience and 7 years' experience in academics and consultancy. His current research interests are Geopolymer Concrete and Earthquake resistance structures.



Ramesh Babu Chokkalingam completed his Ph.D. from IIT Chennai. He has more than ten years of experience in teaching and research. His areas of research includes pervious concrete, geopolymer concrete, and high volume flyash concrete.



Dr.M.Shanmugasundaram: He had completed his B.E degree in Civil Engineering from RCET Madurai, M.E in Structural Engineering, TCE Madurai. He completed his Ph.D in 2014 under the esteemed guidance of Dr. K.Sudalaimani, Professor, TCE, Madurai. He has 30+ international research publications to his credits. He had filed three