

Nanocrystalline CuCo_2Se_4 Thin Film Counter Electrode for Dye-Sensitized Solar Cells

A. Murugan, V. Siva, A. Shameem, S. Asath Bahadur



Abstract: Nanocrystalline CuCo_2Se_4 thin film have been deposited on over the micro slide by simplest route of successive ionic layer adsorption and reaction (SILAR) method. The CuCo_2Se_4 film was understand by Structural, morphological, and optical. The X-ray diffraction analyses confirm the formation of Cubic crystalline structure, than calculated grain size, dislocation density, and microstrain. The morphology of the film is homogeneous and agglomerated surface. The annealed CuCo_2Se_4 film are shows good optical absorption and the optical energy band gap energy is 1.90 eV, thus the suitable candidates for dye-Sensitized solar cell (DSSCs) application.

Keywords: CuCo_2Se_4 , SILAR, DSSCs, UV-Vis.

I. INTRODUCTION

Last few years energy demand due to increasing population. Limitations on the conventional energy sources, the focus on maximum consumption of the solar energy. Now days silicon based material are used to photovoltaic application, it have more expensive. Therefore need for economical materials if possible of direct optical energy band gap materials. DSSCs, is one of the most hopeful solar cells, DSSCs is overcome by silicon based solar cell such as ease to manufacture and low cost. DSSC is constructed with a counter electrode (CE), a redox-couple electrolyte, natural or organic based dyes and a working electrode, it made-up by sandwiched between the electrodes [1]. Platinum (Pt) free CE electrodes have been used in research laboratory due to its outstanding performance of chemical stability and electro catalytic activity. Unluckily, the high cost and low present ratio at earth and its produce a difficulty for large-scale application of DSSCs. Therefore improvement of low-priced CE materials

with extraordinary electro catalytic activity and significance for real-world applications. The most of CE are used to carbon, conductive polymers, metal compounds, and graphene, like oxide, nitride, carbide, selenide and sulfide [2]-[8].

The metal selenides is a great attention due to their unique electronic properties, stimulating chemical behaviors, and wide multiplicity of application. Nanocrystalline CuCo_2Se_4 thin film have been deposited on to micro slide by SILAR method. SILAR is mostly unique because of homogenous deposition is possible on complex shape, its simplicity and deposited large area, economical cost and operating low temperature [9]. Annealed film was analysis by Structural, functional group, morphological, and optical properties. Ternary CuCo_2Se_4 film have good absorption in and the optical energy band gap is calculated by using Tauc's plot and obtained band gap is 1.90 eV suitable candidates for solar cell application.

II. EXPERIMENTAL

A. Material and methods

The Nano-crystalline CuCo_2Se_4 thin film was deposited on to glass substrate by SILAR method. Copper chloride, cobalt chloride, and sodium selenite anhydrous were used as analytical grade reagent and without any further purification for this film deposition. Double distilled (DD) water, ethanol were used as a solvent and washing of glass substrate.

The substrate is commercially available micro glass slide and the size of dimensions 25mm x 75mm x 1.5mm. The substrate activation process begin with etching the substrate, the substrate dipped in chromic acid for 3 minutes, then rinsed with double distilled water, and substrate dipped vertically in dilute HF for 2 minutes, then the substrate rinsed with DD water and finally substrate was ultrasonically cleaned under the DD water bath for 30 minutes.

The cation precursor solution was initially prepared by Cu^{2+} solution and Co^{2+} solution in separate beaker are stirrer for 30 minutes. Then the Cu solution is added drop wise in to Co solution under the stirring condition. After mixing the cation solution was stirred for an hour. The anion (Na_2SeO_3) solution was prepared by single bath which stirred in one hour. Both precursor solutions are prepared in 50 ml double distilled water. Both cation (pH=6) and anion (pH=7) precursor solution are maintained in stable pH at the end of the film deposition process. Precursor solution was taken 2:1:3 ratio of Cu, Co, and Se. The cationic and anionic precursor solution dissolved in 50 ml of double distilled water. Immersion of the cleaned substrate in cationic precursor solution for 30s ions was adsorbed on active center of the substrate surface.

Manuscript published on 30 December 2019.

* Correspondence Author (s)

S. Asath Bahadur*, Department of Physics, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India, and Condensed Matter Physics Laboratory, International Research Centre, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India.

Email: s_a_bahadur@yahoo.co.in

A. Murugan, Department of Physics, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India, and Condensed Matter Physics Laboratory, International Research Centre, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India. Email: murugan027@gmail.com

V. Siva, Department of Physics, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India, and Condensed Matter Physics Laboratory, International Research Centre, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India. Email: vsiva33.physics@gmail.com

A. Shameem, Department of Physics, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India, and Condensed Matter Physics Laboratory, International Research Centre, Kalasalingam Academy of Research and Education, Krishnankoil-626 126, India. Email: shameemirfu@gmail.com

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](https://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

Then the substrate was rinsed in DD water for 20s to remove the loosely adsorbed cation from the surface of the substrate and to get the homogeneity. The substrate was subsequently dipped in the anionic solution for 30s. The sulfide ions reacted with adsorbed cations on the substrate surface. Finally substrate was rinsed in DD water for 20s to remove the unreacted cation, anion and powder particles from the substrate. Both rinsing water bath are maintained at 65 °C.

The above mention four steps for one SILAR cycle than similarly to 40 cycles were deposit by CuCo_2Se_4 thin film. After complete deposition, film was dried at 60 °C under the vacuum oven for one hour. The film was annealed at 300 °C for 2 h in muffle furnace at air atmosphere. In this SILAR method pH, temperature of the precursor solutions, concentration, and immersing period duration are significant parameter. The film was deposited on both side of the glass substrate.

B. Characterization

The CuCo_2Se_4 thin film structural was confirmed by powder X-ray diffraction (Bruker D8 advance ECO systems). The morphology and elemental confirmation can be investigated by scanning electron microscope (ZEISS EVO 18). The functional group analysis by Fourier transform infrared spectra (FT-IR) of the film were taken wavenumber from 4000–400 cm^{-1} (Shimadzu-IR Tracer-100). Optical absorption of the film were carried out in the wavelength range of 300–1100 nm using UV–Vis. spectrophotometer (Shimadzu-1800).

III. RESULT AND DISCUSSION

A. Structural analysis

Figure 1 shows the XRD patterns of the annealed CuCo_2Se_4 thin film. The XRD peaks reveal the crystalline nature of CuCo_2Se_4 with a cubic structure having (006) preferential orientation. The observed XRD peaks at 2θ value 31.89, correspond to (006) planes. The observations are in good agreement with the literature [10], [11]. The grain size (D) is calculated by scherrer formula [12]

$$D = \frac{0.9 \lambda}{\beta \cos \theta}$$

where, λ is the wavelength of the Cu $K\alpha$ X-ray source, β is the full width at the half maximum, θ is the bragg’s angle. The calculated grain size of the annealed CuCo_2Se_4 film is 57nm. The structural parameters of CuCo_2Se_4 film have been calculated by dislocation density and microstrain, evaluated from the equation.

$$\delta = \frac{1}{D^2}$$

$$\epsilon = \frac{\beta \cos \theta}{4}$$

The micro strain and dislocation density calculated values is 0.0029 $\text{line}^{-2} \text{m}^{-4}$ and $1.16788 \times 10^{15} \text{ lines/m}^2$ respectively.

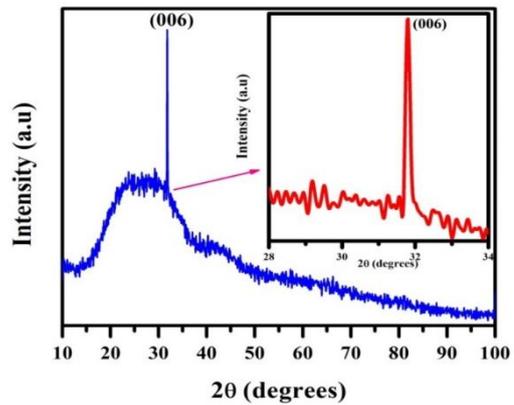


Fig. 1. Powder XRD pattern of CuCo_2Se_4 thin film

B. Fourier transform infrared spectra

FT-IR spectrum of CuCo_2Se_4 thin film taken in the range 4000–400 cm^{-1} shows in Figure 2. The functional groups of substrate surface bound molecules are identified by FTIR. Expected functional groups were present and metal selenium vibration at 669 cm^{-1} is assigned to the Co-Se vibration.

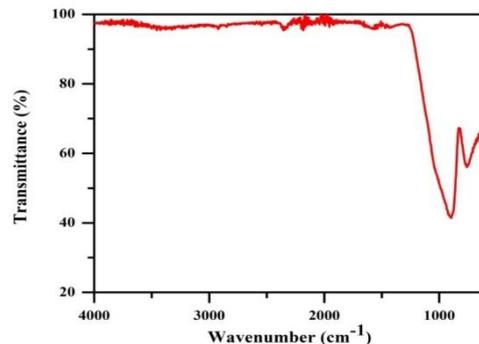


Fig. 2. FTIR spectrum of CuCo_2Se_4 thin film

C. Surface morphology analysis

The CuCo_2Se_4 film surface morphology of the annealed film has taken from SEM is show in Figure 3. From this micrograph, it is evident that the surface has well deposited agglomerated surface and without any visible cracks or holes which is suitable for solar cell application. The CuCo_2Se_4 film surface is covered partly by sphere-shaped micro-crystallites and the size of the sphere-shaped particle are roughly calculated nearby 200 nm.

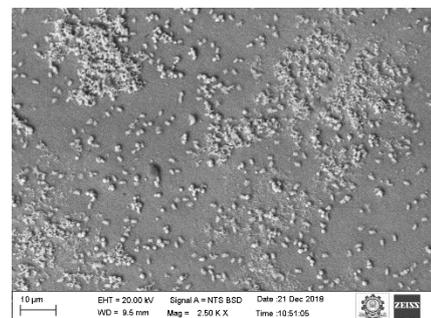


Fig. 3. SEM image of the CuCo_2Se_4 thin film

C. Optical properties

Figure 4 shows the UV-Vis absorbance spectra of CuCo₂Se₄ film. The deposited film shows good absorption in the visible region, spectrum range 400 to 800 nm confirm that is a good applicant for economic and environment friendly solar cell absorber layer and has suitable band gap for thin film solar cell. The band gap of the material formed in the deposits is calculated from the optical energy band gap using Tauc's plot [13].

$$\alpha = \frac{A(E - E_g)^n}{E}$$

From equation α is the absorption coefficient, E is the photon energy (eV), E_g is the optical energy band gap (eV). The superscript n, is a constant which given the values is 1/2, 3 and 3/2 for direct, indirect and indirect forbidden allowed respectively. Figure 5 show in the Tauc's plots for the annealed CuCo₂Se₄ film. The optical energy band gap of the CuCo₂Se₄ film is calculated as 1.90 eV, which is required for any solar cell material.

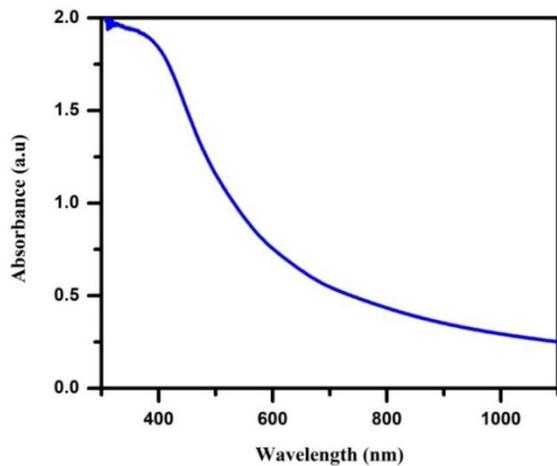


Fig. 4. UV-Vis absorbance spectrum of CuCo₂Se₄ thin film

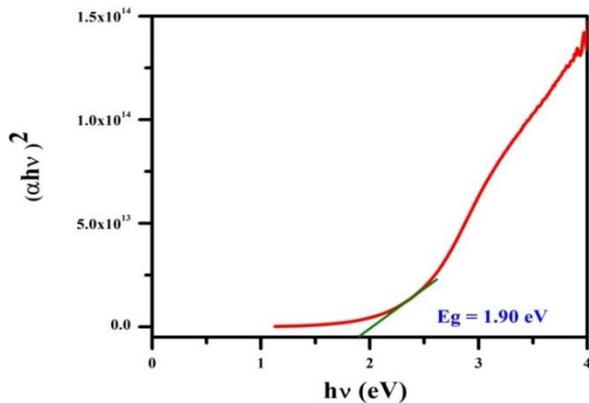


Fig. 5. Tauc's plot

IV. CONCLUSION

The CuCo₂Se₄ thin film have been deposited over on micro glass substrate by SILAR method. Powder XRD shows good crystalline nature and grain size of the CuCo₂Se₄ thin film evaluate by Scherrer's equation as 57 nm. The morphology of annealed film shows spherical particle on the substrate and well uniformly deposited without any crack.

Optical property of the film shows good absorbance in visible wavelength it is suitable for solar cell absorber material because the optical energy band gap is 1.90 eV. Therefore, the CuCo₂Se₄ system may be an attractive choice for counter electrode in DSSCs.

ACKNOWLEDGMENT

The author A. Murugan and S. Asath Bahadur are thankful to Department of Science and Technology-Science and Engineering Research Board (DST-SERB) - New Delhi, for the financial support (No : EMR/2016/006874).

REFERENCES

- Hong Sun, Lu Zhang and Zhong-Sheng, "Wang Single-crystal CoSe₂ nanorods as an efficient electrocatalyst for dye-sensitized solar cells," *J. Mater. Chem. A.*, vol. 2, Jul. 2014, pp.16023-16029
- K. Suzuki, M. Yamaguchi, M. Kumagai and S. Yanagida, "Application of carbon nanotubes to counter electrodes of dye-sensitized solar cells," *Chem. Lett.*, vol. 32(1), Sep. 2002, pp.28-29
- L. Kavan, J. H. Yum and M. Gratzel, *Nano Lett.*, 2011, 11, 5501. "Graphene nanoplatelets outperforming platinum as the electrocatalyst in co-bipyridine-mediated dye-sensitized solar cells," *Nano letters.*, vol. 11(12), Nov. 2011, pp.5501-5506
- H. Wang, Q. Feng, F. Gong, Y. Li, G. Zhou and Z.-S. Wang, "In situ growth of oriented polyaniline nanowires array for efficient cathode of Co (III)/Co (II) mediated dye-sensitized solar cell," *J. Mater. Chem. A.*, vol.1(1), Nov. 2013, pp.97-104.
- J. Xia, C. Yuan and S. Yanagida, "Novel counter electrode V2O5/Al for solid dye-sensitized solar cells," *ACS Appl. Mater. Interfaces.*, vol. 2(7), Jul. 2010, pp.2136-2139.
- G. Li, J. Song, G. Pan and X. Gao, "Highly Pt-like electrocatalytic activity of transition metal nitrides for dye-sensitized solar cells," *Energy Environ. Sci.*, vol. 4(5), Mar. 2011, pp.1680-1683.
- M. Wu, X. Lin, A. Hagfeldt and T. Ma, "Low-cost molybdenum carbide and tungsten carbide counter electrodes for dye-sensitized solar cells," *Angewandte Chemie International Edition.*, vol. 50(15), 2011, pp.3520-3524.
- F. Gong, H. Wang, X. Xu, G. Zhou and Z.-S. Wang, "In situ growth of Co_{0.85}Se and Ni_{0.85}Se on conductive substrates as high-performance counter electrodes for dye-sensitized solar cells. *J. Am. Chem. Soc.*, vol. 134(26), 2012, pp.10953-10958.
- A. Shameem, P. Devendran, V. Siva, M. Raja, S.A. Bahadur, and A. Manikandan, "Preparation and characterization studies of nanostructured CdO thin films by SILAR method for photocatalytic applications," *Journal of Inorganic and Organometallic Polymers and Materials.*, vol. 27(3), May. 2017, pp.692-699
- Pinjiang Li and Qunwei Tang, "Highly transparent metal selenide counter electrodes for bifacial dyesensitized solar cells," *Journal of Power Sources.*, vol.317, Jun. 2016, pp.43-48
- Biplab K. Deka, Ankita Hazarika, Jisoo Kim, Namhun Kim, Hoon Eui Jeong, Young-Bin Park, and Hyung Wook Park, "Bimetallic copper cobalt selenide nanowire-anchored woven carbon fiberbased structural supercapacitors," *Chemical Engineering Journal.*, vol. 355, Jan. 2019, pp.551-559
- S. Das, K. Sa, P.C. Mahakul, J. Raiguru, I. Alam, B.V.R.S. Subramanyam, and P. Mahanandia, "Synthesis of quaternary chalcogenide CZTS nanoparticles by a hydrothermal route. *In IOP Conference Series: Materials Science and Engineering.*, Vol. 338, Mar. 2018, pp. 012062
- R. Sani, R. Manivannan, S.N. Victoria, "One step electrochemical deposition of czts for solar cell applications," *Chalcogenide Lett.*, vol. 14 (5), May. 2017, pp. 165-170

AUTHORS PROFILE



A. Murugan is a Senior Research Fellow in the Department of Physics at Kalasalingam Academy of Research and Education. He has joined as Junior Research Fellow in the Department of Physics under DST-SERB funded project, Govt. of India in the year of 2017. He has received his Master's Degree in Physics from Government Arts College (Autonomous), Coimbatore, which is affiliated to Bharathiar University in the year 2013. His research focus is thin film for solar cell applications and the design of materials enhanced for energy applications.



Dr. V. Siva obtained Ph.D in Physics from Kalasalingam Academy of Research and Education in 2018. He has received his Bachelor's Degree and Master's Degree in Physics from Government Arts College (Autonomous), Coimbatore, which is affiliated to Bharathiar University in the years 2010 and 2012, respectively. He has expertise in the areas of Crystallography, Crystal growth and Computational Physics. To his credit, he has published more than 20 articles in journals of international repute besides ten more as proceedings. Further, he has presented papers in various conferences and seminars. His current research interest is development of Metal-Organic Frameworks (MOFs) for sensor and energy storage application.



A. Shameem is a Research scholar in the Department of Physics, School of Advanced Sciences at Kalasalingam Academy of Research and Education, India. He received his B.Sc. degree in Physics from Jamal Mohamed College, Tiruchirappalli, in 2010, and his M.Sc. degree in Physics from Government Arts College (Autonomous), Coimbatore, in 2012. His research interest is in the field of nanomaterials for energy and environmental applications.



Dr. S. Asath Bahadur is a Senior Professor in the Department of Physics, School of Advanced Sciences at Kalasalingam Academy of Research and Education, India. He has obtained Ph.D in the area of X-ray crystallography from Madurai Kamaraj University in 1994 and also received his M.Phil and M.Sc. Degree in physics from Madurai Kamaraj University. He has expertise in the areas of Crystallography and Material science. He has published more than eighty five peer review research articles in journals of international repute besides seventy more as proceedings.